

TS 753


.T6

Copy 1





DIAMOND DESIGN

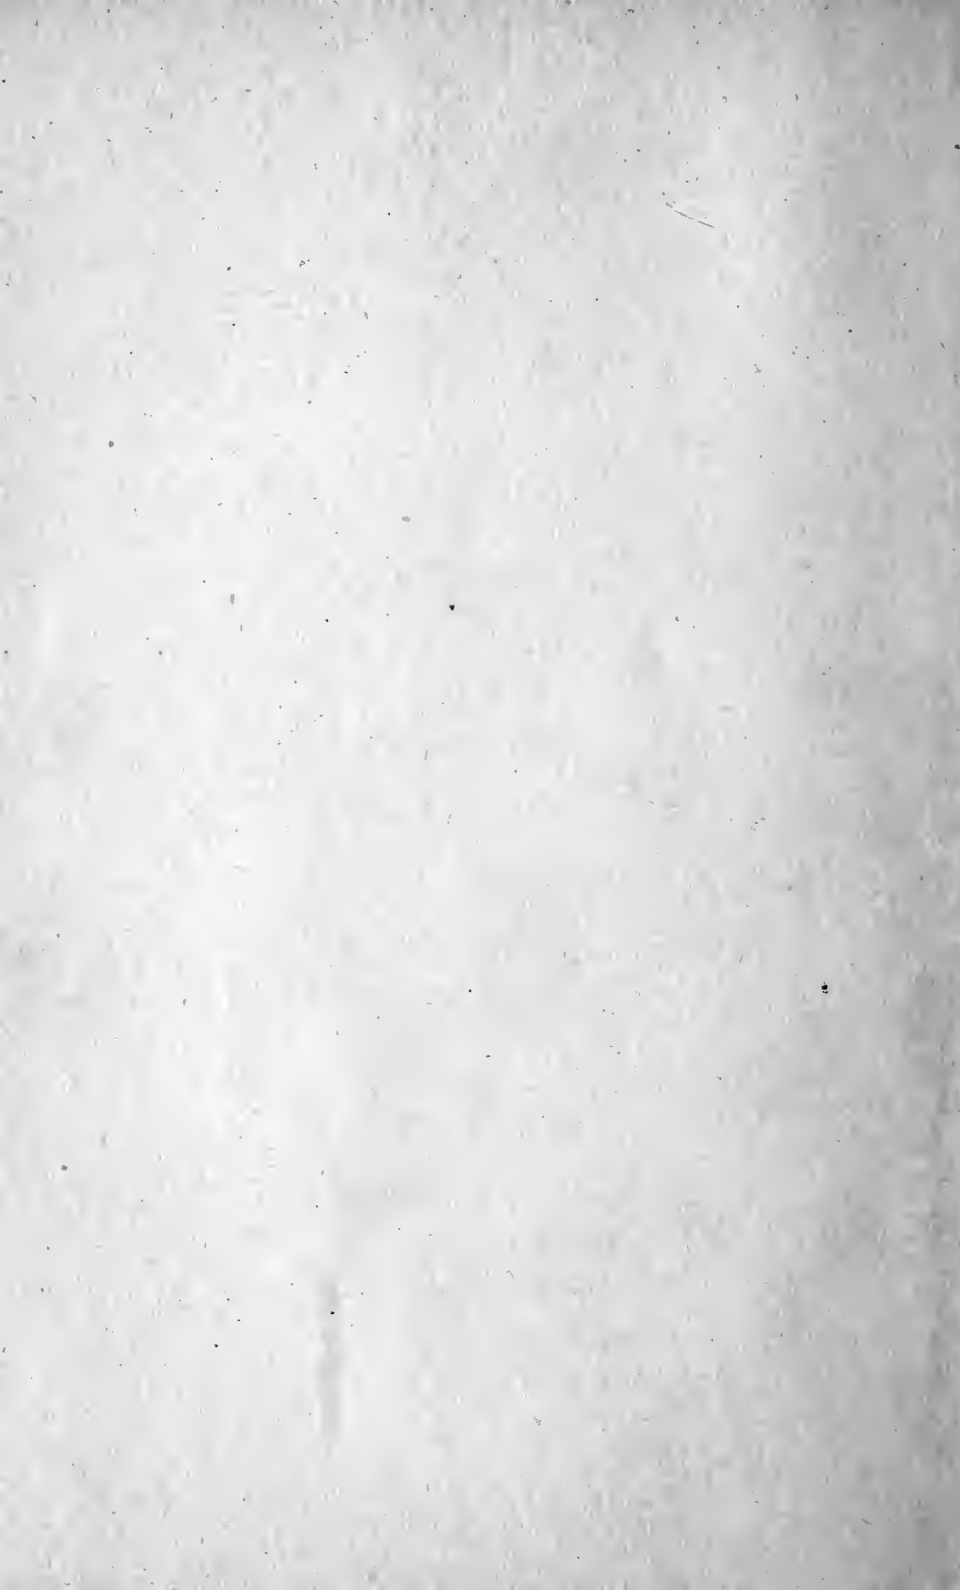

DIAMOND DESIGN

A STUDY OF THE REFLECTION
AND REFRACTION OF LIGHT IN
A DIAMOND

BY

MARCEL TOLKOWSKY

B.Sc., A.C.G.I.

WITH 37 ILLUSTRATIONS



London:

E. & F. N. SPON, LTD., 57 HAYMARKET, S.W. 1

New York:

SPON & CHAMBERLAIN, 120 LIBERTY STREET

1919

TS 753

.T6

404593

31



31-13446

T. Sch. Mar. 30, 19

CONTENTS

	PAGE
INTRODUCTION	5
PART I.—HISTORICAL	8
„ II.—OPTICAL	26
„ III.—MATHEMATICAL	53
THE ROSE	59
THE BRILLIANT	64
<i>A. Back</i>	64
<i>B. Front</i>	80
FACETING	94
BEST PROPORTIONS OF A BRILLIANT	97

DIAMOND DESIGN

INTRODUCTION

THIS book is written principally for students of precious stones and jewellers, and more particularly for diamond manufacturers and diamond cutters and polishers. The author will follow the evolution of the shape given to a cut diamond, and discuss the values of the various shapes and the reason for the discarding of the old shapes and the practically universal adoption of the brilliant.

It is a remarkable fact that, although the art of cutting a diamond has been known for more than two thousand years, it is entirely empirical, and that, though many keen contemporary minds have been directed upon the diamond, and the list of books written on that subject increases rapidly, yet

nowhere can one find any mathematical work determining the best shape for that gem. The present volume's chief aim is the calculation of that shape.

The calculations have been made as simple as possible, so as not to be beyond the range of readers with a knowledge of elementary geometry, algebra, and trigonometry. Where, however, it was found that the accuracy of the results would be impaired without the introduction of more advanced mathematics, these have been used, and graphical methods have been explained as an alternative.

The results of the calculations for the form of brilliant now in use were verified by actual mensuration from well-cut brilliants. The measures of these brilliants are given at the end of the volume both in a tabulated and in a graphical form. It will be seen how strikingly near the actual measures are to the calculated ones.

The method used in the present work will be found very useful for the design of other transparent precious and semi-

precious stones, although it will be found advisable in the case of stones of an agreeable colour to cut the gem somewhat thicker than the calculations warrant, so as to take full advantage of the colour. The same remark applies to diamonds of some exceptional and beautiful colour, like blue or pink, where the beauty or the value of the stone increases with the depth of its colour.

Part I

HISTORICAL

IT is to Indian manuscripts and early Indian literature we turn when we want to find the origin of diamond cutting, for India has always been regarded as the natural and ancient home of the diamond. It is there that they were first found: up to 1728, the date of the discovery of the Brazilian deposits, practically the whole world's supply was derived from Indian sources. They are found there in the valleys and beds of streams, and also, separated from the matrix in which they were formed, in strata of detrital matter that have since been covered by twelve to sixteen feet of earth by the accumulation of later centuries. Diamonds have existed in these deposits within the reach of man for many ages, but the knowledge

of the diamond as a gem or as a crystal with exceptional qualities does not go back in India to the unfathomable antiquity ~~to~~ which books on diamonds generally refer ~~to~~. It was wholly unknown in the Vedic period, from which no specific names for precious stones are handed down at all.¹ The earliest systematic reference appears to be in the *Arthaśāstra* of Kautilya (about third century B.C.), where the author mentions six kinds of diamonds classified according to their mines, and describes them as differing in lustre and hardness. He also writes that the best diamonds should be large, regular, heavy, capable of bearing blows,² able to scratch metal,

¹ Berthold Laufer, *The Diamond: a Study in Chinese and Hellenistic Folklore* (Chicago, 1915).

² This legend of the indestructibility of the diamond, which reappears in many other places, and to which the test of the diamond's capacity of bearing the strongest blows was due, has caused the destruction of perhaps a very large number of fine stones. The legend was further embroidered by the remark that if the diamond had previously been placed in the fresh and still warm blood of a ram, it could then be broken, but with great difficulty. This legend was

refractive and brilliant. In the *Milinda-pañha* (Questions of King Milinda) (about first century B.C.) we read that the diamond ought to be pure throughout, and that it is mounted together with the most costly gems. This is the first manuscript in which the diamond is classed as a gem.

It is therefore permissible to estimate with a sufficient degree of accuracy that the diamond became known in India during the Buddhist period, about the fourth century B.C., and that its use as a gem dates from that period.¹

It is not known with certainty when and where the art of grinding or polishing diamonds originated. There is as yet no source of ancient Indian literature in which the polishing of diamonds is distinctly set forth, although the fact that diamond is used for grinding gems generally is men-

still current in Europe as late as the middle of the thirteenth century. The actual fact is that the diamond, although exceedingly hard (it is the hardest substance known), can easily be split by a light blow along a plane of crystallisation.

¹ Laufer, *loc. cit.*

tioned. It is, however, likely that, where the polishing of other precious stones was accomplished in that manner, that of diamonds themselves cannot have been entirely unknown. What polishing there was must at first have been limited to the smoothing of the faces of the crystals as they were found. The first description of cut diamonds is given by Tavernier,¹ a French jeweller who travelled through India, and to whom we owe most of our knowledge of diamond cutting in India in the seventeenth century. At the time of his visit (1665) the Indians were polishing over the natural faces of the crystal, and preferred, therefore, regularly crystallised gems. They also used the knowledge they had of grinding diamonds to remove faulty places like spots, grains, or glesses. If the fault was too deep, they attempted to hide it by covering the surface under which it lay with a great number of small facets. It appears from Tavernier's writings that

¹ Tavernier, *Voyage en Turquie, en Perse et aux Indes* (1679).

there were also European polishers in India at that time, and that it was to them the larger stones were given for cutting. Whether they had learnt the art independently or from Indians and attained greater proficiency than they, or whether they were acting as instructors and teaching the Indians a new or a forgotten art, is uncertain. Both views are equally likely in the present state of research upon that subject: at the time of Tavernier's visit, diamond cutting had been known in Europe for more than two centuries.

Among the several remarkable gems that

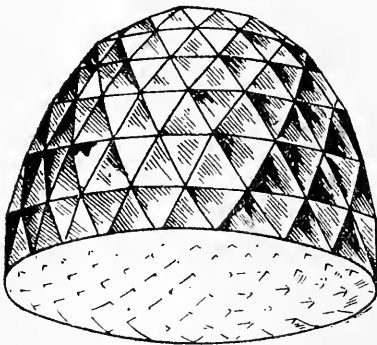


FIG. I.

Tavernier describes, the most noteworthy is the one known as the Great Mogul. This diamond was of a weight of 280 cts. and was cut as sketched in fig. I.

The polishing was the work of a Venetian, Hortensio Borgis, to whom it was given for that purpose by

its owner, the Great Mogul Aurung Zeb, of Delhi. This kind of cut is characteristic of most of the large Indian stones, such as the Orlov (fig. 2), which is now the largest diamond of the Russian

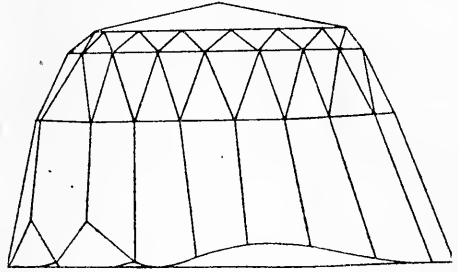


FIG. 2.

crown jewels and weighs $193\frac{3}{4}$ cts. The Koh-i-Noor (fig. 3), now among the British crown jewels, was of a somewhat similar shape before recutting. It weighed then 186 cts.

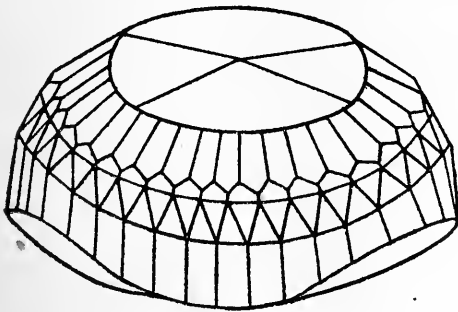


FIG. 3.

Tavernier also mentions several other types of cut which he met in India.

The Great Table (fig. 4), which he saw in 1642, weighed 242 cts. Both the Great Table and the Great Mogul seem to have disappeared: it is not known what has become of them since the seventeenth century.

Various other shapes are described, such as point stones, thick stones, table stones


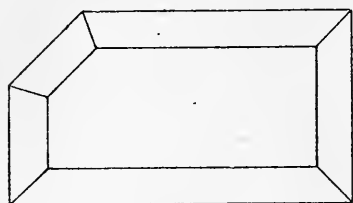


FIG. 4.

(fig. 5), etc. But the chief characteristic remains: all these diamonds have been cut with one aim constantly in view—how

to polish the stone with the smallest possible loss of weight. As a consequence the polishing was generally accomplished by covering the surface of the stone with a large number of facets, and the original shape of the rough gem was, as far as possible, left unaltered.



It was mentioned before that the art of diamond polishing had already been known in



FIG. 5.

Europe for several centuries when Tavernier left for India. We have as yet no certain source of information about diamond cutting in Europe before the fourteenth century. The first reference thereto mentions that diamond polishers were work-

ing in Nurnberg (Germany) in 1375, where they formed a guild of free artisans, to which admission was only granted after an apprenticeship of five to six years.¹ We do not know, however, in what shape and by what method the stones were cut.

It is in the fifteenth century that European diamond cutting begins to become more definite, more characteristic. And it is from that time that both on its technical and artistic sides progress is made at a rate, slow at first, but increasing rapidly later.

It is not difficult to find the chief reason for that change.

Up to that time, diamonds had almost exclusively been used by princes or priests. To princes they were an emblem of power and wealth—in those days diamonds were credited with extraordinary powers: they were supposed to protect the wearer and to bring him luck. Princes also found them convenient, as they have great value

¹ Jacobson's *Technologisches Wörterbuch* (1781).

for a very small weight, and could easily be carried in case of flight. Priests used them in the ornaments of temples or churches; they have not infrequently been set as eyes in the heads of statues of Buddha.

In the fifteenth century it became the fashion for women to wear diamonds as jewels. This fashion was started by Agnes Sorel (about 1450) at the Court of Charles VII of France, and gradually spread from there to all the Courts of Europe.

This resulted in a very greatly increased demand, and gave a strong impulse to the development of diamond polishing. The production increased, more men applied their brains to the problems that arose, and, as they solved them and the result of their work grew better, the increasing attractiveness of the gem increased the demand and gave a new impulse to the art.

At the beginning of the fifteenth century a clever diamond cutter named Hermann established a factory in Paris, where his

work met with success, and where the industry started developing.

In or about 1476 Lodewyk (Louis) van Berquem, a Flemish polisher of Bruges, introduced absolute symmetry in the disposition of the facets, and probably also improved the process of polishing. Early authors gave credence to the statement of one of his descendants, Robert van Berquem,¹ who claims that his ancestor had invented the process of polishing the diamond by its own powder. He adds: "After having ground off redundant material from a stone by rubbing it against another one (the process known in modern practice as 'bruting' or cutting), he collected the powder produced, by means of which he polished the diamond on a mill and certain iron wheels of his invention."

¹ Robert de Berquem, *Les merveilles des Indes: Traité des pierres précieuses* (Paris, in-4°, 1669), p. 12: "Louis de Berquem l'un de mes ayeuls a trouvé le premier l'invention en mil quatre cent soixante-seize de les tailler avec la poudre de diamant même. Auparavant on fut contraint de les mettre en œuvre tels qu'on les rencontrait aux Indes, c'est-

As has already been shown, we know now that diamonds were polished at least a century before Lodewyk van Berquem lived. And as diamond is the hardest substance known, it can only be polished by its own powder. Van Berquem cannot thus have invented that part of the process. He may perhaps have introduced some important improvement like the use of cast-iron polishing wheels, or possibly have discovered a more porous kind of cast iron—one on which the diamond powder finds a better hold, and on which polishing is therefore correspondingly speedier.

à-dire tout à fait bruts, sans ordre et sans grâce, sinon quelques faces au hasard, irrégulières et mal polies, tels enfin que la nature les produit. Il mit deux diamants sur le ciment et après les avoir égrisés l'un contre l'autre, il vit manifestement que par le moyen de la poudre qui en tombait et à l'aide du moulin et certaines roues de fer qu'il avait inventées, il pourrait venir à bout de les polir parfaitement, même de les tailler en telle manière qu'il voudrait. Charles devenu duc de Bourgogne lui mit trois grands diamants pour les tailler avantageusement selon son adresse. Il les tailla aussitôt, l'un épais, l'autre faible et le troisième en triangle et il y réussit si bien que le duc, ravi d'une invention si surprenante, lui donna 3000 ducats de récompense."

What Van Berquem probably did originate is, as already stated, rigid symmetry in the design of the cut stone. The introduction of the shape known as *pendeloque* or *briolette* is generally ascribed to him. The Sancy and the Florentine, which are both cut in this shape, have been said

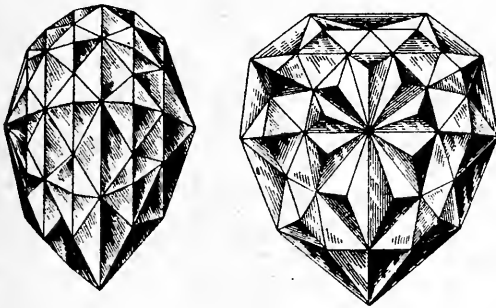


FIG. 6.

by some to have been polished by him. The Sancy ($53\frac{3}{4}$ cts.) belongs now to the Maharaja of Guttiola, and the Florentine (fig. 6), which is much larger ($133\frac{1}{5}$ cts.), is at present among the Austrian crown jewels. The history of both these gems is, however, very involved, and they may have been confused at some period or other with similar stones. That is why it is not at all certain that they were

the work of Van Berquem. At any rate, they are typical of the kind of cut he introduced.

The pendeloque shape did not meet with any very wide success. It was adopted in the case of a few large stones; but was gradually abandoned, and is not used to any large extent nowadays, and then in a modified form, and only when the shape of the rough stone is especially suitable. This unpopularity was largely due to the fact that, although the loss of weight in cutting was fairly high, the play of light within the stone did not produce sufficient fire or brilliancy.

About the middle of the sixteenth century a new form of cut diamond was introduced. It is known as the *rose* or *rosette*, and was made in various designs and proportions (figs. 7 and 8). The rose spread rapidly and was in high vogue for about a century, as it gave a more pleasant effect than the pendeloque, and could be cut with a much smaller loss of weight. It was also found very advantageous in the polishing of flat

pieces of rough or split diamond. Such material is even now frequently cut into roses, chiefly in the smaller sizes.




FIG. 7.

In the chapter upon the design of diamonds it will be shown that roses have to be made thick (somewhat thicker than in fig. 7) for the loss of light to be small, and that the flatter the rose the bigger the loss of light. It will also be seen there that the fire of a rose cannot be very high. These faults caused the rose to be superseded by the brilliant.

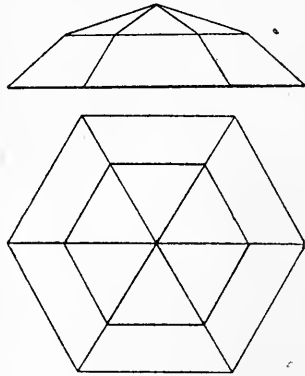


FIG. 8.

We owe the introduction of the brilliant in the middle of the seventeenth century to Cardinal Mazarin—or at any rate to his influence. As a matter of fact, the first brilliants were known as Mazarins, and were

of the design of fig. 9. They had sixteen facets, excluding the table, on the upper side.

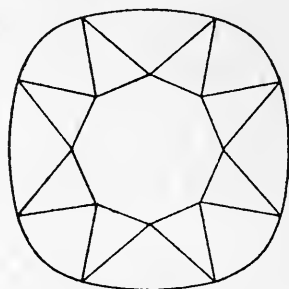


FIG. 9.

They are called double-cut brilliants. Vincent Peruzzi, a Venetian polisher, increased the number of facets from sixteen to thirty-

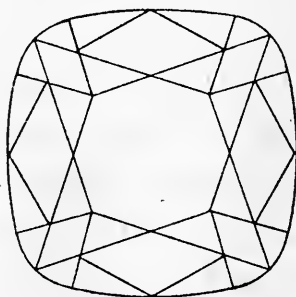


FIG. 10.

two (fig. 10) (triple-cut brilliants), thereby increasing very much the fire and brilliancy of the cut gem, which were already in the double-cut brilliant incomparably better

than in the rose. Yet diamonds of that cut, when seen nowadays, seem exceedingly dull compared to modern-cut ones. This dullness is due to their too great thickness, and to a great extent also to the difference in angle between the corner facets and the side facets, so that even if the first were

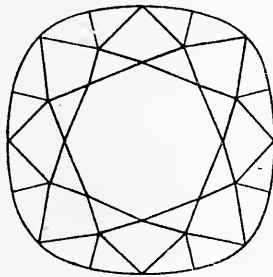


FIG. II.

polished to the correct angle (which they were not) the second would be cut too steeply and give an effect of thickness. Old-cut brilliants, as the triple-cut brilliants are generally called, were at first modified by making the size and angle of the facets more uniform (fig. II), this bringing about a somewhat rounder stone. With the introduction of mechanical bruting or cutting (an operation distinct from polishing; see

p. 17) diamonds were made absolutely circular in plan (fig. 37). The gradual shrinking-in of the corners of an old-cut brilliant necessitated a less thickly cut stone with a consequent increasing fire and life, until a point of maximum brilliancy was reached. This is the present-day brilliant.¹

Other designs for the brilliant have been tried, mostly attempts to decrease the loss of weight in cutting without impairing the brilliancy of the diamond, but they have not met with success.

We may note here that the general trend of European diamond polishing as opposed to Indian is the constant search for greater brilliancy, more life, a more

¹ Some American writers claim that this change from the thick cut to that of maximum brilliancy was made by an American cutter, Henry D. Morse. It was, however, as explained, *necessitated* by the absolute roundness of the new cut. Mr Morse may have invented it independently in America. But it is highly probable that it originated where practically all the world's diamonds were polished, in Amsterdam or Antwerp, where also mechanical bruting was first introduced.

vivid fire in the diamond, regardless of the loss of weight. The weight of diamond removed by bruting and by polishing amounts even in the most favourable cases to 52 per cent. of the original rough weight for a perfectly cut brilliant. In the next chapters the best proportions for a brilliant will be calculated without reference to the shape of a rough diamond, and it will be seen how startlingly near the calculated values the modern well-cut brilliant is polished.

Part II

OPTICAL

It is to light, the play of light, its reflection and its refraction, that a gem owes its brilliancy, its fire, its colour. We have therefore to study these optical properties in order to be able to apply them to the problem we have now before us: the calculation of the shape and proportions of a perfectly cut diamond.

Of the total amount of light that falls upon a material, part is returned or reflected; the remainder penetrates into it, and crosses it or is absorbed by it. The first part of the light produces what is termed the "lustre" of the material. The second part is completely absorbed if the material is black. If it is partly absorbed the material will appear coloured,

and if transmitted unaltered it will appear colourless.

The diamonds used as gems are generally colourless or only faintly coloured ; it can be taken that all the light that passes into the stones passes out again. The lustre of the diamond is peculiar to that gem, and is called adamantine for that reason. It is not found in any other gem, although zircon and demantoid or olivine have a lustre approaching somewhat to the adamantine.

In gem stones of the same kind and of the same grade of polish, we may take it that the lustre only varies with the area of the gem stone exposed to the light, and that it is independent of the type of cut or of the proportions given to the gem (in so far as they do not affect the area) ; this is why gems where the amount of light that is reflected upon striking the surface is great, or where much of the light that penetrates into the stone is absorbed and does not pass out again, are frequently cut in such shapes as the cabochon (fig. 12),

so as to get as large an area as possible, and in that way take full advantage of the lustre.

In a diamond, the amount of light reflected from the surface is much smaller than that penetrating into the stone; moreover, a diamond is practically perfectly transparent, so that all the light that passes into the stone has to pass out again. This



FIG. 12.

is why lustre may be ignored in the working out of the correct shape for a diamond, and why any variation in the amount of light reflected from the exposed surface due to a change in that surface may be considered as negligible in the calculations.

The brilliancy or, as it is sometimes termed, the "fire" or the "life" of a gem thus depends entirely upon the play of light in the gem, upon the path of rays of light in the gem. If a gem is so cut or designed that every ray of light passing

into it follows the best path possible for producing pleasing effects upon the eye, then the gem is perfectly cut. The whole art of the lapidary consists in proportioning his stone and disposing his facets so as to ensure this result.

If we want to design a gem or to calculate its best shape and proportions, it is clear that we must have sufficient knowledge to be able to work out the path of any ray of light passing through it. This knowledge comprises the essential part of optics, and the laws which have to be made use of are the three fundamental ones of reflection, refraction, and dispersion.

REFLECTION

Reflection occurs at the surface which separates two different substances or media ; a portion or the whole of the light striking that surface is thrown back, and does not cross over from one medium into another. This is the reflected light. There are different kinds of reflected light according to the nature of the surface of reflection. If

that surface is highly polished, as in the case of mirrors, or polished metals or gems, the reflection is perfect and an image is formed. The surface may also be dull or matt to a greater or smaller extent (as in the case of, say, cloth, paper, or pearls). The reflected light is then more or less scattered and diffused.

It is the first kind of reflection that is of importance to us here, as diamond, owing to its extreme hardness, takes a very high grade of polish and keeps it practically for ever.

The laws of reflection can be studied very simply with a few pins and a mirror placed at right angles upon a flat sheet of paper.

A plan of the arrangement is shown in fig. 13. The experiment is as follows :—

I. A straight line A B is drawn upon the paper, and the mirror is stood on the paper so that the plane of total reflection (*i.e.* the silvered surface) is vertically over that line. Two pins P and Q are stuck anyhow on the paper, one as near the mirror and the other as far away as possible.

Then the eye is placed in line with PQ at 1, so that Q is hidden by P . Without moving the eye, two more pins R and S are inserted, one near to and the other far from the mirror, in such positions that

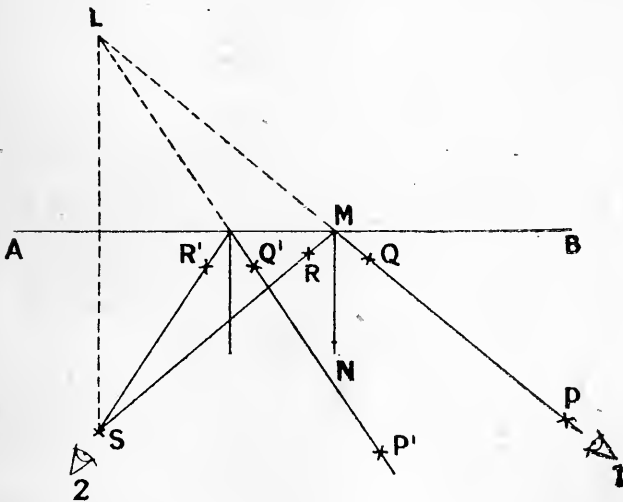


FIG. 13.

their images appear in the mirror to lie along PQ continued.

If the eye is now sighted from position 2 along SR , Q and P will appear in the mirror to lie on SR continued.

The mirror is now removed, PQ and SR are joined and will be found to intersect on AB at M . If a perpendicular MN be

erected on AB at that point, the angles NMP and NMS will be found equal.

The above experiment may be repeated along other directions, but keeping the pin S at the same point. The line of sight will now lie on $P'Q'$, and the angles between $P'Q'$, SR' and the normal will again be found equal.

In the first experiment S appeared to lie on the continuation of PQ , in the second it appears to be situated on $P'Q'$ produced. Its image is thus at the intersection of these two lines, at L . It can easily be proved by elementary geometry (from the equality of angles) that the image L of the pin is at the same distance from the mirror as the pin S itself, and is of the same size.

II. If the pins P, Q, R, S in the first experiment be placed so that their heads are all at the same height above the plane sheet of paper, and the eye be placed in a line of sight with the heads P, Q , the images of the heads R, S in the mirror will be hidden by the head of pin P .

The angle NMP (position I) is called

angle of incidence, and the angle NMS angle of reflection.

The laws of reflection (verified by the above tests) can now be formulated as follows :—

I. The angle of reflection is equal to the angle of incidence.

II. The paths of the incident and of the reflected ray lie in the same plane.

From I it follows, as shown, that

III. The image formed in a plane reflecting surface is at the same distance from that surface as the object reflected, and is of the same size as the object.

REFRACTION

When light passes from one substance into another it suffers changes which are somewhat more complicated than in the case of reflection. Thus if we place a coin at the bottom of a tumbler which we fill with water, the coin appears to be higher than when the tumbler was empty; also, if we plunge a pencil into the water, it will seem to be bent or broken at the surface,

except in the particular case when the pencil is perfectly vertical.

We can study the laws of refraction in a manner somewhat similar to that adopted for the reflection tests. Upon a flat sheet of paper (fig. 14) we place a fairly thick

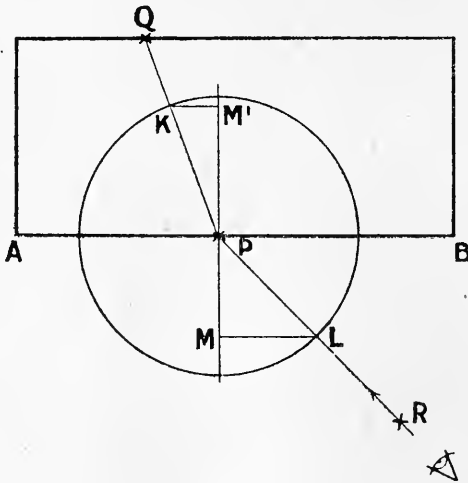


FIG. 14.

rectangular glass plate with one of its edges (which should be polished perpendicularly to the plane of the paper) along a previously drawn line AB . We place a pin, P , close to the edge AB of the glass plate and another, Q , close to the further edge. Looking through the surface AB ,

we place our eye in such a position that the pin Q as viewed through the glass is covered by pin P. Near to the eye and on the same line of sight we stick a third pin R, which therefore covers pin P. The glass plate is now removed. PQ and PR are joined, a perpendicular to AB, MM', is erected at P, and a circle of any radius drawn with P as centre. This circle cuts PQ at K and RP at L. LM and KM' are drawn perpendicular to MM', LM and KM' are measured and the ratio $\frac{LM}{KM'}$ found.

The experiment is repeated for different positions of P and Q and the corresponding ratio $\frac{LM}{KM'}$ calculated. It will be found that for a given substance (as in this case glass) this ratio is constant. It is called the index of refraction, and generally represented by the letter n .

Referring to fig. 14, we note that as

$$PK = PL = \text{radius of the circle,}$$

we can write

$$\frac{LM}{KM'} = \frac{\frac{LM}{PL}}{\frac{PK}{KM'}} = \frac{\sin RPM}{\sin QPM'}$$

Writing the angle of incidence RPM as i , and the angle of refraction QPM' as r , this equation becomes

$$n = \frac{\sin i}{\sin r} \quad . \quad . \quad . \quad (1)$$

or

$$n \sin r = \sin i \quad . \quad . \quad . \quad (2)$$

In this case the incident ray is in air, the index of refraction of which is very nearly unity. With another substance it can be shown that equation (2) becomes

$$n \sin r = n' \sin i \quad . \quad . \quad . \quad (3)$$

where n' is the index of refraction of that substance.

It can be seen easily, and in a way similar to that used with reflection (*i.e.* sighting along the heads of the pins), that, in refraction also :

The paths of the incident and of the refracted ray lie in the same plane.

Of two substances with different index of refraction, that which has the greater index of refraction is called optically denser. In the experiment the light passed from air to glass, which is of greater optical density. Let us now consider the reverse case, *i.e.*

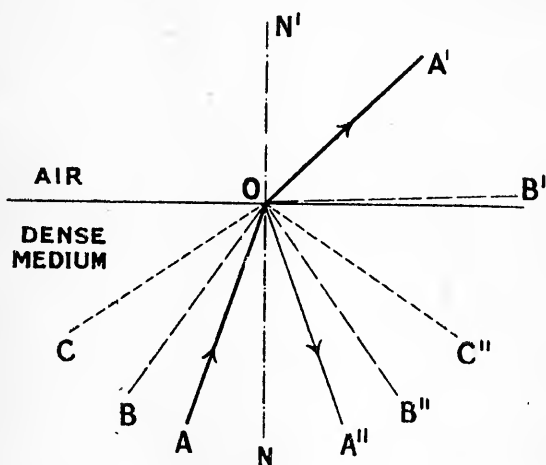


FIG. 15.

when light passes from one medium to another less dense optically. Suppose a beam of light AO (fig. 15) with a small angle of incidence passes from water into air. At the surface of separation a small proportion of it is reflected to A'' (as we have seen under reflection). The remainder is refracted in a direction OA' which is

more divergent from the normal $NO N'$ than AO .

Suppose now that the angle AON gradually increases. The proportion of reflected light also increases, and the angle of refraction $N'OA'$ increases steadily and at a more rapid rate than NOA , until for a certain value of the angle of incidence BON the refracted angle will graze the surface of separation. It is clear that under these conditions the amount of light which is refracted and passes into the air is zero. If the angle of incidence is still greater, as at CON , there is no refracted ray, and the whole of the light is reflected into the optically denser medium, or, as it is termed, total reflection then occurs. The angle BON is called critical angle, and can easily be calculated by (3) when the refractive indices n and n' are known. It will be noted that when the angle of incidence attains its critical value i' , the angle of refraction becomes a right angle, *i.e.* its sine becomes equal to unity.

Substituting in (3)

$$\begin{aligned} n \sin r &= n' \sin i' \\ \sin r &= 1 \\ \sin i' &= \frac{n}{n'} \quad . \quad . \quad . \quad (4) \end{aligned}$$

Or, if the less dense medium be air,

$$\begin{aligned} n &= 1 \\ \sin i' &= \frac{1}{n'} * \quad . \quad . \quad . \quad (5) \end{aligned}$$

This formula (5) is very important in the design of gems, for by its means the critical angle can be accurately calculated. A precious stone, especially a colourless and transparent one like the diamond, is cut to the best advantage and with the best possible effect when it sends to the spectator as strong and as dazzling a beam of light as possible. Now a gem, not being in itself a source of light, cannot shine with other than reflected light. The maximum amount of light will be given off by the gem

* No mention is made here of double refraction, as the diamond is a singly refractive substance, and it was considered unnecessary to introduce irrelevant matter.

if the whole of the light that strikes it is reflected by the back of the gem, *i.e.* by that part hidden by the setting, and sent out into the air by its front part. The facets of the stone must therefore be so disposed that no light that enters it is let out through its back, but that it is wholly reflected. This result is obtained by having the facets inclined in such a way that all the light that strikes them does so at an angle of incidence greater than the critical angle. This point will be further dealt with in a later chapter.

The following are a few indices of refraction which may be useful or of interest :—

Water	1·33
Crown glass	1·5 approx.
Quartz	1·54–1·55
Flint glass	1·576
Colourless strass	1·58
Spinel	1·72
Almandine	1·79
Lead borate	1·83
Demantoid	1·88

Lead silicate	2.12	
Diamond	2.417	(6)

These indices have, of course, been found by methods more accurate than the tests described. One of these methods, one particularly suitable for the accurate determination of the indices of refraction in gems, will be explained later.

With this value for the index of refraction of diamond, the critical angle works out at

$$\begin{aligned} \sin i &= \frac{1}{n} \\ &= \frac{1}{2.417} = .4136 \\ i &= \sin^{-1} .4136 \\ i &= 24^{\circ} 26' . \quad . \quad . \quad (7) \end{aligned}$$

This angle will be found very important.

DISPERSION

What we call white light is made up of a variety of different colours which produce white by their superposition. It is to the

decomposition of white light into its components that are due a variety of beautiful phenomena like the rainbow or the colours of the soap bubble—and, it may be added, the “fire” of a diamond.

The index of refraction is found to be different for light of different colours, red being generally refracted least and violet most, the order for the index of the various colours being as follows :—

Red, orange, yellow, green, blue, indigo, violet.

Note.—In the list given above the index of refraction is that of the yellow light obtained by the incandescence of a sodium salt. This colour is used as a standard, as it is very bright, very definite, and easily produced.

If white light strikes a glass plate with parallel surfaces (fig. 20) the different colours are refracted as shown when passing into the glass. Now for every colour the angle of refraction is given by (equation (2))

$$n \sin r = \sin i.$$

When passing out of the glass, the angle of refraction is given by

$$n \sin i' = \sin r'.$$

As the faces of the glass are parallel, $i' = r$.

Therefore, $r' = i$, and the ray when leaving the glass is parallel to its original direction. The various colours will thus follow parallel

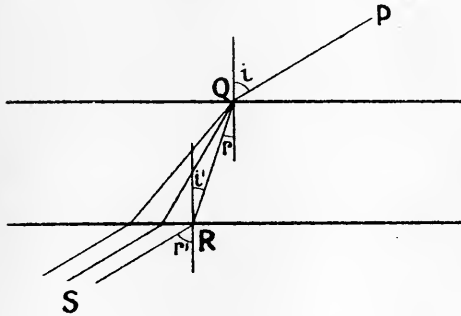


FIG. 16.

paths as shown in fig. 16, and as they are very near together (the dispersion is very much exaggerated), they will strike the eye together and appear white. This is why in the pin experiments on refraction, dispersion was not apparent to any extent.

If, instead of using parallel surfaces as in a glass plate, we place them at an angle, as in a prism, light falling upon a face of

the prism will be dispersed as shown in fig. 17; and, when leaving by another face, the light, instead of combining to form white (as in a plate), is still further dispersed and forms a ribbon of lights of the different

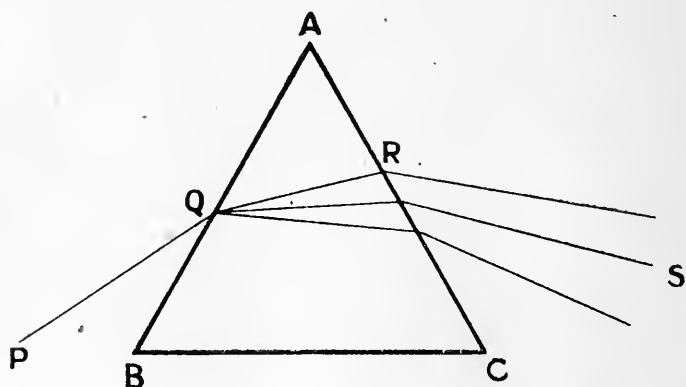


FIG. 17.

colours, from red to violet. Such a ribbon is called a spectrum. The colours of a spectrum cannot be further decomposed by the introduction of another prism.

The difference between the index of refraction of extreme violet light and that of extreme red is called dispersion.¹ Dis-

¹ Generally two definite points on the spectrum are chosen; the values given here for gems are those between the B and G lines of the solar spectrum.

persion, on the whole, increases with the refractive index, although with exception. The dispersion of a number of gems and glasses is given below :—

Quartz	·013
Sapphire	·018
Crown glass	·019
Spinel	·020
Almandine	·024
Flint glass	·036
Diamond	·044
Demantoid	·057

The greater the dispersion of a medium, other things being equal, the greater the difference between the angles of refraction of the various colours, and the further separated do they become. It is to its very high dispersion (the greatest of all colourless gem-stones) that the diamond owes its extraordinary "fire." For when a ray of light passes through a well-cut diamond, it is refracted through a large angle, and consequently the colours of the spectrum, becoming widely separated, strike

a spectator's eye separately, so that at one moment he sees a ray of vivid blue, at another one of flaming scarlet or one of shining green, while perhaps at the next instant a beam of purest white may be reflected in his direction. And all these colours change incessantly with the slightest motion of the diamond.

The effect of refraction in a diamond can be shown very interestingly as follows:— A piece of white cardboard or fairly stiff paper with a hole about half an inch in diameter in its centre is placed in the direct rays of the sun or another source of light. The stone is held behind the paper and facing it in the ray of light which passes through the hole. A great number of spots of the most diverse colours appear then upon the paper, and with the slightest motion of the stone some vanish, others appear, and all change their position and their colour. If the stone is held with the hand, its slight unsteadiness will give a startling appearance of life to the image upon the paper. This life is one of the

chief reasons of the diamond's attraction, and one of the main factors of its beauty.

MEASUREMENT OF REFRACTION

In the study of refraction it was pointed out that the manner by which the index of refraction was calculated there, although the simplest, was both not sufficiently accurate and unsuitable for gem-stones. One of the best methods, and perhaps the one giving the most correct results, is that known as method of minimum deviation. Owing to the higher index of refraction of diamond it is especially suitable in its case, where others might not be convenient.

The theory of that method is as follows :—

Let ABC be the section of a prism of the substance the refraction index of which we want to calculate (fig. 18). A source of light of the desired colour is placed at R , and sends a beam RI upon the face AB of the prism. The beam RI is broken, crosses the prism in the direction II' , is again broken, and leaves it along $I'R'$. Supposing now that we rotate prism ABC

about its edge A. The direction of $I'R'$ changes at the same time; we note that as we gradually turn the prism, $I'R'$ turns in a certain direction. But if we go on turning the prism, $I'R'$ will at a certain moment stop and then begin to turn in

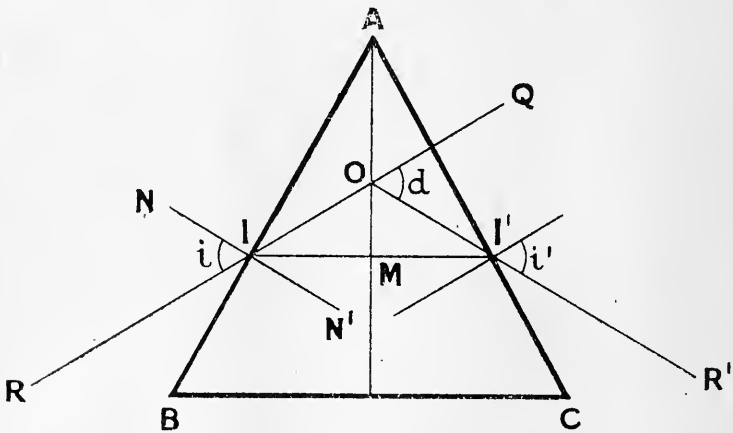


FIG. 18.

the reverse direction, although the rotation of the prism was not reversed. We also note that at the moment when the ray is stationary the deviation has attained its smallest value. It is not difficult to prove that this is the case when the ray of light passes through the prism symmetrically, *i.e.* when angles i and i' (fig. 18) are equal.

Let AM be a line bisecting the angle A . Then II' is perpendicular to AM . Let RI be produced to Q and $R'I'$ to O . They meet on AM and the angle QOR' is the deviation d (*i.e.* the angle between the original and the final direction of the light passing through the prism).

Therefore $OII' = \frac{1}{2}d$.

Draw the normal at I , NN' .

Then

$$MIN' = IAM = \frac{1}{2}a$$

if a be the angle BAC of the prism.

Now by equation (1)

$$n = \frac{\sin i}{\sin r}$$

$$\begin{aligned} i = NIR = OIN' &= OIM + MIN' \\ &= \frac{1}{2}d + \frac{1}{2}a = \frac{1}{2}(d+a) \end{aligned}$$

$$r = MIN' = \frac{1}{2}a$$

therefore

$$n = \frac{\sin \frac{1}{2}(d+a)}{\sin \frac{1}{2}a} \quad (8)$$

The index of refraction can thus be calculated if the angles d and a are known. These are found by means of a spectroscope.

This instrument consists of three parts : the collimator, the table, and the telescope. The light enters by the collimator (a long brass tube fitted with a slit and a lens) passes through the prism which is placed on the table, and leaves by the telescope. The collimator is usually mounted rigidly upon the stand of the instrument. Its function is to determine the direction of entry of the light and to ensure its being parallel. Both the table and the telescope are movable about the centre of the table, and are fitted with circular scales which are graduated in degrees and parts of a degree, and by means of which the angles are found.

Now two facets of a stone are selected, and the stone is placed upon the table so that these facets are perpendicular to the table. The angle a of the prism, *i.e.* the angle between these facets, can be found by direct measurement with a goniometer or also by the spectroscope. The angle d is found as follows :—The position of the stone is arranged so that the light after

passing through the collimator enters it from one selected facet and leaves it by the other. The telescope is moved until the spectral image of the source of light is found. The table and the stone are now rotated in the direction of minimum devia-

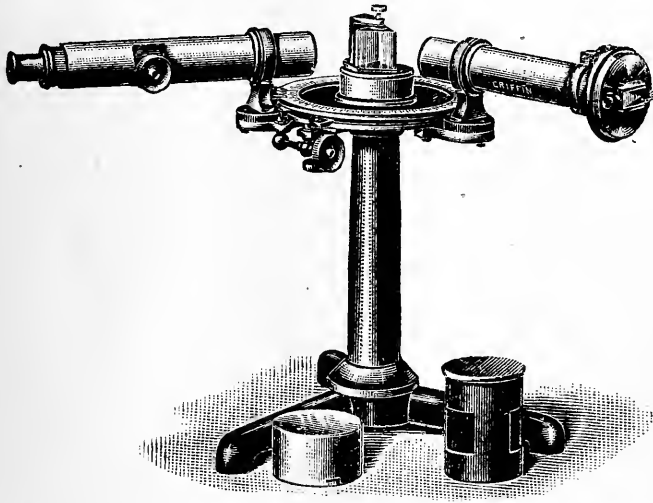


FIG. 19.

tion, and at the same time the telescope is moved so that the image is kept in view. We know that at the point of minimum deviation the direction of motion of the telescope changes. When this exact point is reached the movements of the stone and of the telescope are stopped, and the

reading of the angle of deviation d is taken on the graduated scale.

The values of a and d are now introduced in equation (8) :

$$n = \frac{\sin \frac{1}{2}(a+d)}{\sin \frac{1}{2}a}$$

and the value of n calculated with the help of sine tables or logarithms.

The values for diamond are

$$n = 2.417 \text{ for sodium light}$$

$$\text{Dispersion} = n_{\text{red}} - n_{\text{violet}} = .044.$$

Part III

MATHEMATICAL

IN the survey of the history of diamond cutting, perhaps the most remarkable fact is that so old an art should have progressed entirely by trial and error, by gradual correction and slow progress, by the almost accidental elimination of faults and introduction of ameliorations. We have traced the history of the art as far back as 1375, when the earliest recorded diamond manufactory existed, and when the polishers had already attained a high degree of guild organisation. We have every reason to believe that the process of diamond polishing was known centuries before. And yet all these centuries, when numerous keen minds were directed upon the fashioning of the gem, have left no single record of

any purposeful planning of the design of the diamond based upon fundamental optics. Even the most bulky and thorough contemporary works upon the diamond or upon gems generally rest content with explaining the basic optical principles, and do no more than roughly indicate how these principles and the exceptional optical properties of the gem explain its extraordinary brilliancy; nowhere has the author seen calculations determining its best shape and proportions. It is the purpose of the present chapter to establish this shape and these proportions. The diamond will be treated essentially as if it were a worthless crystal in which the desired results are to be obtained, *i.e.* without regard to the great value which the relation between a great demand and a very small supply gives to the least weight of the material.

It is useful to recall here the principles and the properties which will be used in the calculations.

Reflection

1. The angles of incidence and of reflection are equal.
2. The paths of the incident and of the reflected ray lie in the same plane.

Refraction

1. When a ray of light passes from one medium into a second of different density, it is refracted as by the following equation :

$$n \sin r = n' \sin i \quad . \quad . \quad (3)$$

where r = angle of refraction.

i = angle of incidence.

n = index of refraction of the second medium.

n' = index of refraction of the first medium.

If the first medium is air, $n' = 1$, and equation becomes

$$n \sin r = \sin i \quad . \quad . \quad (2)$$

2. When a ray of light passes from one medium into another optically less dense, total reflection occurs for all values of the angle of incidence above a certain critical

value. This critical angle is given by equation

$$\sin i' = \frac{n}{n'} \quad (4)$$

Or, if the less dense medium be air,

$$\sin i' = \frac{1}{n'} \quad (5)$$

3. The paths of the incident and of the refracted ray lie in the same plane.

Dispersion

When a ray of light is refracted, dispersion occurs, *i.e.* the ray is split up into a band or spectrum of various colours, owing to the fact that each colour has a different index of refraction. The dispersion is the difference between these indices for extreme rays on the spectrum.

Data

In a diamond :

Index of refraction : $n = 2.417$ (for a sodium light)

dispersion : $\delta = .044$

critical angle : $i' = 24^\circ 26'$. (7)

DETERMINATION OF THE BEST ANGLES
AND THE BEST PROPORTIONS

Postulate.—The design of a diamond or of any gem-stone must be symmetrical about an axis, for symmetry and regularity in the disposition of the facets are essential for a pleasing result.

Let us now consider a block of diamond bounded by polished surfaces, and let us consider the effect on the path of light of a gradual change in shape; we will also observe the postulate and keep the block symmetrical about its axis.

Let us take as first section one having parallel faces (fig. 20), and let MM' be its axis of symmetry. Let us for convenience place the axis of symmetry vertically in all future work, so that surfaces crossing it are horizontal.

Consider a ray of light SP striking face AB . It will be refracted along PQ and leave by QR , parallel to SP (as we have seen in studying dispersion). We also know that if NN' is the normal at Q , angles

$\angle NQP$ and $\angle QPM'$ are equal. Therefore, for total reflection,

$$\angle QPM' = 24^\circ 26',$$

but at that angle of refraction the angle of incidence $\angle SPM$ becomes a right angle and no light penetrates into the stone. It is thus obvious that parallel faces in a gem

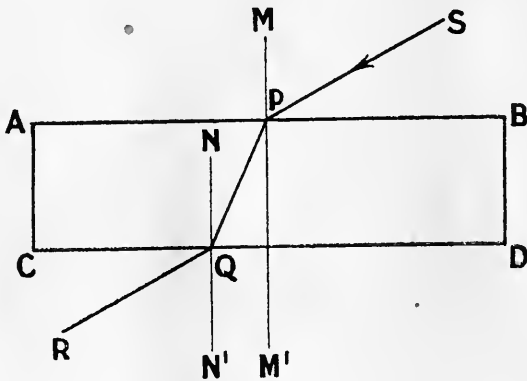


FIG. 20.

are very unsatisfactory, as all the light passing in by the front of a gem passes out again by the back without any reflection.

We can avoid parallelism by inclining either the top or the bottom faces at an angle with the direction AB . In the first case we obtain the shape of a rose-cut diamond and in the second case that of a

brilliant cut. We will examine the rose cut in the first instance.

THE ROSE

Consider (fig. 21) a section having the bottom surface horizontal, and let us incline

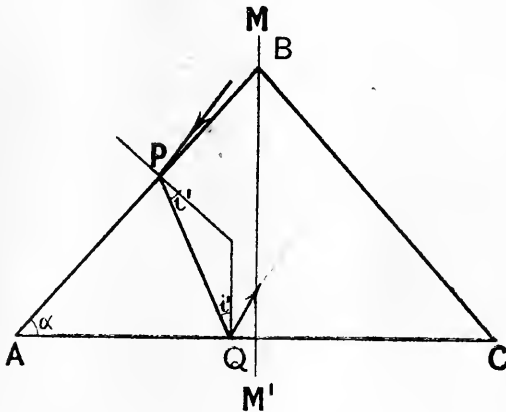


FIG. 21.

the top surface AB at an angle α with it. To maintain symmetry, another surface BC is introduced. We have now to find the value of α for which total reflection occurs at AC . Now for this to be the case, the minimum angle of incidence upon AC must be $24^{\circ} 26'$. Let us draw such an incident ray PQ . To ensure that no light

is incident at a smaller angle, we must make the angle of refraction at entry $24^{\circ} 26'$ and arrange the surface of entry as shown, AB , for we know that then no light will enter at an angle more oblique to AB or more vertical to AC . This gives to α a value of twice the critical angle, *i.e.* $48^{\circ} 52'$. Such a section is very satisfactory indeed as regards reflection, as, owing to its derivation, all the light entering it leaves by the front part. Is it also satisfactory as regards refraction?

Let us follow the path of a ray of light of any single colour of the spectrum, $SPQRT$ (fig. 22). Let i and r be the angles of incidence upon and of refraction out of the diamond.

At Q , $PQN = RQN$, and therefore in triangles APQ and RCQ

$$\text{angle } AQP = \text{angle } CQR.$$

Also by symmetry $A = C$,
therefore

$$\text{angle } APQ = \text{angle } CRQ;$$

it follows that $i = r$.

As the angle i is the same for all colours of a white ray of light, the various colours will emerge parallel out of the diamond and give white light. This is the fundamental reason of the unpopularity of the rose ; there is no fire.

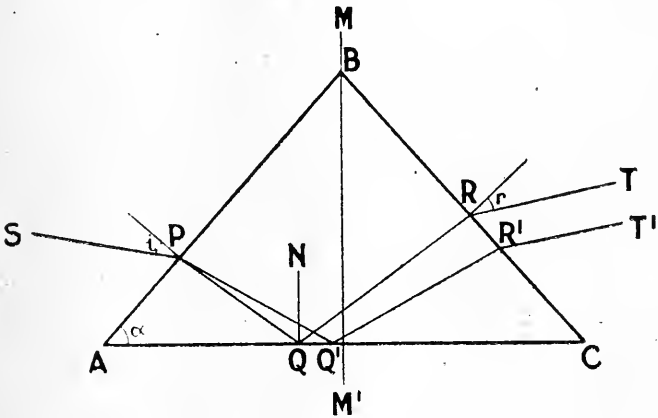


FIG. 22.

This effect may be remedied to a small extent by breaking the inclined facet (figs. 23 and 24), so that the angle be not the same at entry as at exit. This breaking is harmful to the amount of light reflected whichever way we arrange it ; if we steepen the facet near the edge, there is a large proportion of light projected backwards and being

lost, for we may take it that the spectator will not look at the rose from the side of the mounting (fig. 23). If, on the other hand, we flatten the apex of the rose (fig. 24) (which is the usual method), a leakage will occur through its base. There is, of course,

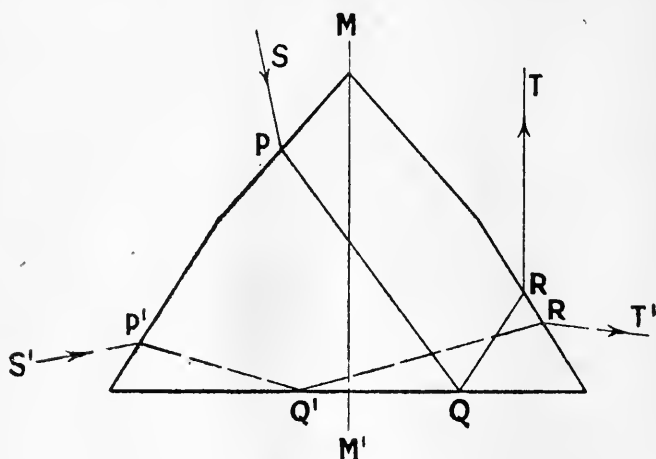


FIG. 23.

no amelioration in the refraction if the light passes from one facet to another similarly placed (as shown in fig. 23, path $S'P'Q'R'T'$). Taking the effect as a whole, the least unsatisfactory shape is as shown in fig. 24, with the angles α about 49° and 30° for the base and the apex respectively. The rose cut, however, is fundamentally

wrong, as we have seen above, and should be abolished altogether. It is the high cost of the material that is the cause of its still being used in cases where the rough shape is especially suitable, and then only in small sizes. In actual practice the

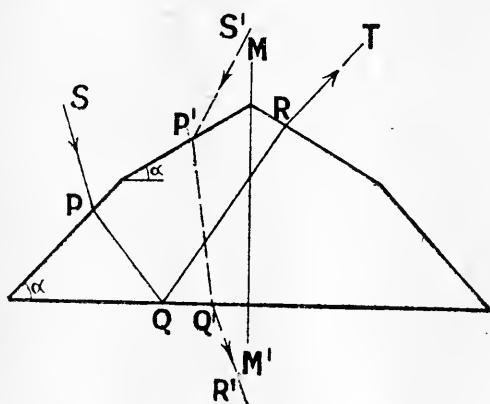


FIG. 24.

proportions of the cut rose depend largely upon those of the rough diamond, the stone being cut with as small a loss of material as possible. Generally the values of α are much below those given above, *i.e.* 49° and 30° , as where the material is thick enough to allow such steep angles it is much better to cut it into a brilliant.

THE BRILLIANT

A. Back of the Brilliant

Let us now pass to the consideration of the other alternative, *i.e.* where the top

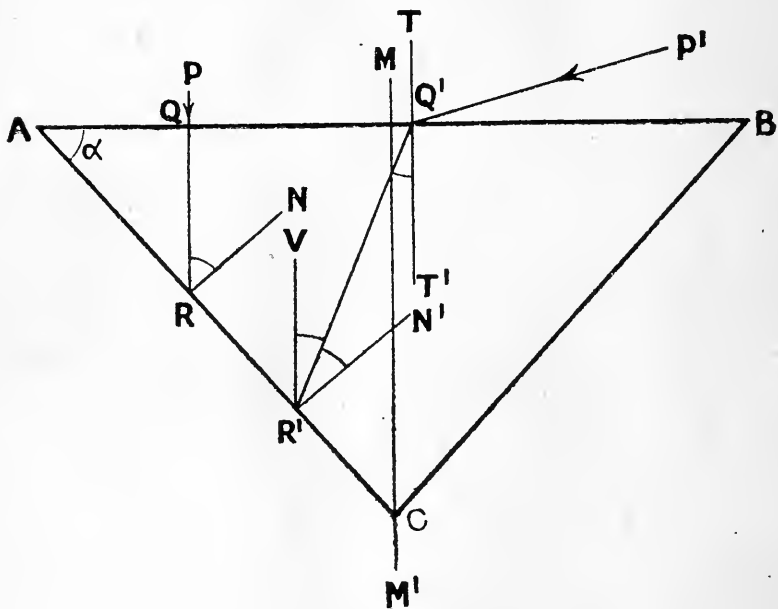


FIG. 25.

surface is a horizontal plane AB and where the bottom surface AC is inclined at an angle α to the horizontal (fig. 25). As before, we have to introduce a third plane BC to have a symmetrical section.

First Reflection

Let a vertical ray PQ strike AB . As the angle of incidence is zero, it passes into the stone without refraction and meets plane AC at R . Let RN be the normal at that point, then, for total reflection to occur,

$$\text{angle } NRQ = 24^\circ 26'.$$

But

$$\text{angle } NRQ = \text{angle } QAR = \alpha,$$

as AQ and QR , AR and RN are perpendicular.

Therefore, for total reflection of a vertical ray,

$$\alpha = 24^\circ 26'.$$

Let us now incline the ray PQ so that it gradually changes from a vertical to a horizontal direction, and let $P'Q'$ be such a ray. Upon passing into the diamond it is refracted, and strikes AC at an angle $Q'R'N'$ where $R'N'$ is the normal to AC . When $P'Q'$ becomes horizontal, the angle of refraction $T'Q'R'$ becomes equal to $24^\circ 26'$. This is the extreme value attain-

able by that angle ; also, for total reflection, angle $Q' R' N'$ must not be less than $24^\circ 26'$. If we draw $R' V$, vertical angle $V R' Q' = R' Q' T' = 24^\circ 26'$, and

$$\begin{aligned} \text{angle } V R' N' &= V R' Q' + Q' R' N' \\ &= 24^\circ 26' + 24^\circ 26' \\ &= 48^\circ 52' \end{aligned}$$

as before,

$$a = \text{angle } V R' N',$$

and therefore

$$a = 48^\circ 52' \quad . \quad . \quad . \quad (9)$$

For absolute total reflection to occur at the first facet, the inclined facets must make an angle of not less than $48^\circ 52'$ with the horizontal.

Second Reflection

When the ray of light is reflected from the first inclined facet AC (fig. 26), it strikes the opposite one BC . Here too the light must be totally reflected, for otherwise there would be a leakage of light through the back of the gem-stone. Let us consider, in the first instance, a ray of light vertically incident upon the stone. The

path of the ray will be PQRST. If RN and SN' are the normals at R and S respectively, then for total reflection,

$$\text{angle } N' S R = 24^\circ 26'.$$

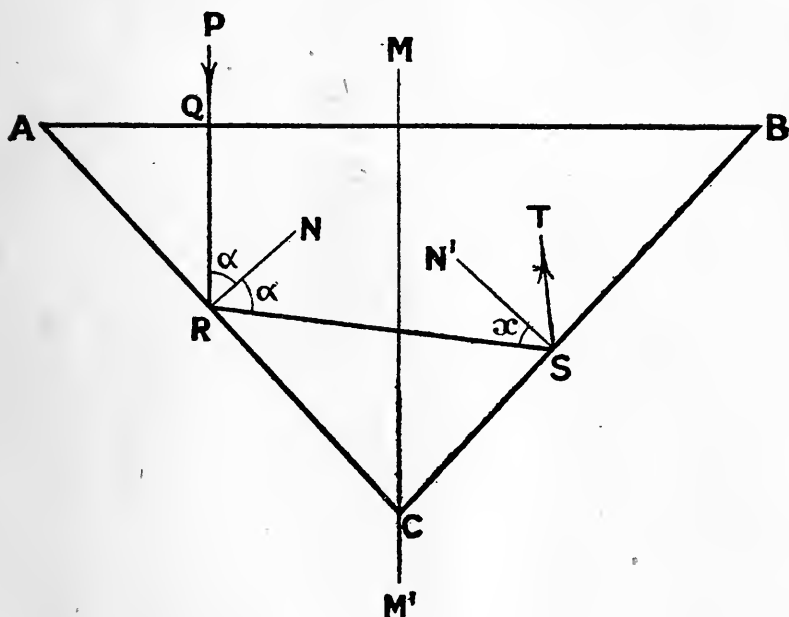


FIG. 26.

Let us find the value of α to fulfil that condition :

$$\text{angle } Q R N = \text{angle } Q A R = \alpha$$

as having perpendicular sides.

$$\text{angle } S R N = \text{angle } Q R N$$

as angles of incidence and reflection.

Therefore

$$\text{angle NRS} = \alpha.$$

Now let

$$\text{angle N'SR} = x$$

Then, in triangle RSC,

$$\text{angle SRC} = 90^\circ - \alpha$$

$$\text{angle RSC} = 90^\circ - x$$

$$\begin{aligned} \text{angle RCS} &= 2 \times \text{angle RCM} \\ &= 2 \times \text{ARQ} = 2(90^\circ - \alpha). \end{aligned}$$

The sum of these three angles equals two right angles,

$$90^\circ - \alpha + 90^\circ - x + 180^\circ - 2\alpha = 180^\circ,$$

or

$$\begin{aligned} 3\alpha + x &= 180^\circ \\ 3\alpha &= 180^\circ - x. \end{aligned}$$

Now, x is not less than $24^\circ 26'$, therefore α is not greater than

$$\alpha = \frac{180 - 24^\circ 26'}{3} = 51^\circ 51'.$$

Let us again incline PQ from the vertical until it becomes horizontal, but in this case in the other direction, to obtain the inferior limit.

Then (fig. 27) the path will be PQR S.
 Let QT, RN, SN' be the normals at Q, R,
 and S respectively. At the extreme case,
 TQR will be $24^{\circ} 26'$. Draw RV vertical
 at R.

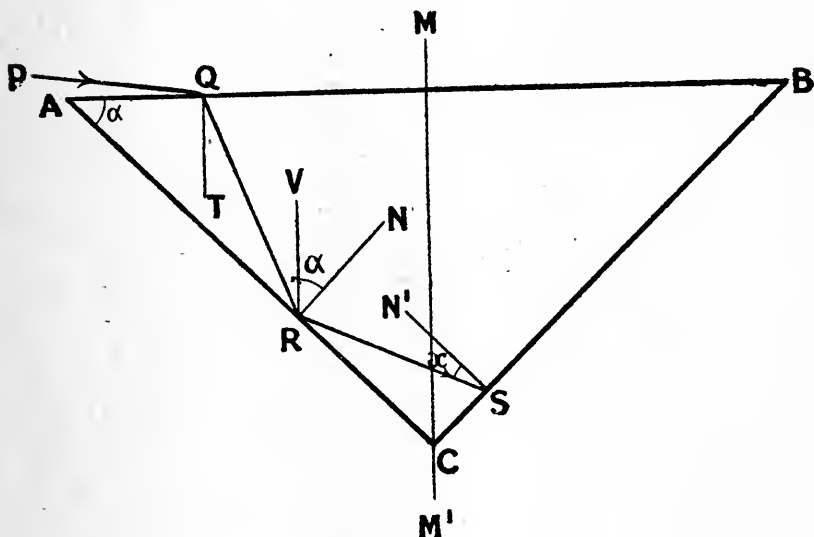


FIG. 27.

Then

$$\text{angle } QR V = \text{angle } TQR = 24^{\circ} 26'$$

$$\text{angle } VRN = a.$$

As before, in triangle RSC,

$$\text{angle } SRC = 90^{\circ} - NRS = 90^{\circ} - a - 24^{\circ} 26'$$

$$\text{angle } RCS = 2(90^{\circ} - a)$$

$$\text{angle } RSC = 90^{\circ} - x.$$

Then

$$90 - a - 24^{\circ} 26' + 180^{\circ} - 2a + 90^{\circ} - x = 180^{\circ}$$

$$3a + x = 180^{\circ} - 24^{\circ} 26' = 155^{\circ} 34'$$

$$3a = 155^{\circ} 34' - x.$$

In the case now considered,

$$x = 24^{\circ} 26'.$$

Then

$$3a = 155^{\circ} 34' - 24^{\circ} 26' = 131^{\circ} 8'$$

$$a = 43^{\circ} 43' \quad . \quad . \quad . \quad . \quad (10)$$

For absolute total reflection at the second facet, the inclined facets must make an angle of not more than $43^{\circ} 43'$ with the horizontal.

We will note here that this condition and the one arrived at on page 66 are in opposition. We will discuss this later, and will pass now to considerations of refraction.

Refraction

First case : a is less than 45°

In the discussion of refraction in a diamond, we have to consider two cases, *i.e.* a is less than 45° or it is more than 45° . Let us take the former case first and let P Q R S T (fig. 28) be path of the ray: Then,

if SN is the normal at S , we know that for total reflection at S angle $RSN = 24^\circ 26'$. We want to avoid total reflection, for if the light is thrown back into the stone, some of it may be lost, and in any case the

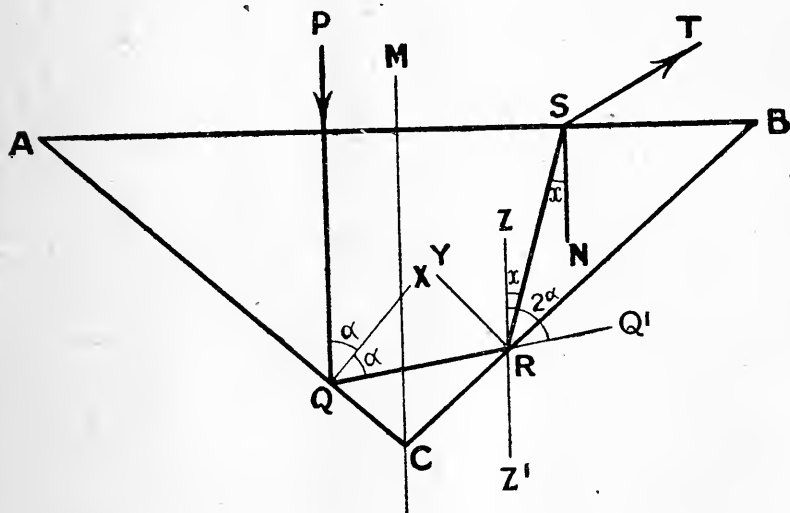


FIG. 28.

ray will be broken too frequently and the result will be disagreeable.

Therefore,

$$\text{angle } RSN < 24^\circ 26' \quad . \quad (II)$$

Suppose this condition is fulfilled and the light leaves the stone along ST . It is refracted, and its colours are dispersed into

a spectrum. It is desirable to have this spectrum as long as possible, so as to disperse the various colours far away from each other. As we know, this will give us the best possible "fire."

This result will be obtained when the ray is refracted through the maximum angle. By (II) the value for that angle is $24^{\circ} 26'$, and (II) becomes

angle $R S N = 24^{\circ} 26'$ for maximum dispersion.

But then the light leaves $A B$ tangentially, and the amount of light passing is zero. To increase that amount, the angle of refraction has to be reduced: the angle of dispersion decreases simultaneously, but the amount of light dispersed increases much more rapidly. Now we know that the angle of dispersion is proportional to the sine of the angle of refraction. It is, moreover, proved in optics that the amount of light passing through a surface as at $A B$ is proportional to the cosine of the angle of refraction. The brilliancy pro-

duced is proportional both to the amount of light and to the angle of dispersion, and therefore to their product, and (by the theory of maxima and minima) will be maximum when they are equal, *i.e.* when the sine and cosine of the angle of refraction are equal. For maximum brilliancy, therefore, the angle of refraction should be 45° . This gives for angle R S N

$$\sin \text{RSN} = \frac{\sin 45}{2.417} = \frac{.7071}{2.417} = .2930,$$

therefore

angle RSN = 17° for optimum brilliancy (12)

Let (fig. 28) Q X and R Y be the normals at Q and R respectively, and let Z Z' be vertical through R.

We know that

$$\text{angle R Q X} = \text{angle P Q X} = \alpha,$$

therefore

$$\text{angle P Q R} = 2\alpha.$$

Produce Q R to Q'.

Then, as P Q and Z Z' are parallel,

$$\text{angle Z R Q}' = \text{angle P Q R} = 2\alpha.$$

Now, let

$$\text{angle R S N} = x (= 17^\circ \text{ for optimum brilliancy}).$$

Then, as $Z Z'$ and $S N$ are parallel,

$$\text{angle Z R S} = x.$$

As they are complements to angles of incidence,

$$\text{angle Q R C} = \text{angle S R B} = i \text{ (say),}$$

but

$$\text{angle Q' R B} = \text{angle Q R C},$$

therefore

$$\text{angle S R Q'} = 2i.$$

In angle $Z R Q'$ we have

$$\begin{aligned} \text{angle Z R Q'} &= \text{angle Z R S} + \text{angle S R Q'} \\ 2\alpha &= x + 2i \quad \cdot \quad \cdot \quad (13) \end{aligned}$$

In triangle $Q C R$

$$\text{angle R C Q} = 90^\circ - \alpha$$

$$\text{angle Q R C} = i$$

$$\text{angle Q C R} = 2(90^\circ - \alpha),$$

therefore

$$(90 - \alpha) + i + 180^\circ - 2\alpha = 180^\circ,$$

or

$$i = 3\alpha - 90^\circ.$$

Introduce this value of i in (13),

$$2\alpha = x + 6\alpha - 180^\circ$$

$$4\alpha = 180^\circ - x$$

and giving x its value 17° ,

$$4\alpha = 180^\circ - 17^\circ = 163^\circ$$

$$\alpha = 40^\circ 45' \quad . \quad . \quad . \quad (14)$$

If we adopt this value for α , the paths of oblique rays will be as shown in fig. 29, P Q R S T when incident from the left of the figure, and P' Q' R' S' T' when incident from the right. Ray P Q R S T will leave the diamond after the second reflection, but with a smaller refraction than that of a vertically incident ray, and therefore with less "fire." Oblique rays incident from the left are, however, small in number owing to the acute angle Q R A with which they strike A C; the loss of fire may therefore be neglected.

Ray P' Q' R' S' T' will strike A B at a greater angle of incidence than $24^\circ 26'$, and will be reflected back into the stone. This is a fault that can be corrected by the introduction of inclined facets D E, F G; ray P' Q' R' S' T' will then strike F G at an

angle less than $24^{\circ} 26'$, and this angle can be arranged by suitably inclining FG to the horizontal so as to give the best possible refraction. The amelioration obtained by thus taking full advantage of the refraction

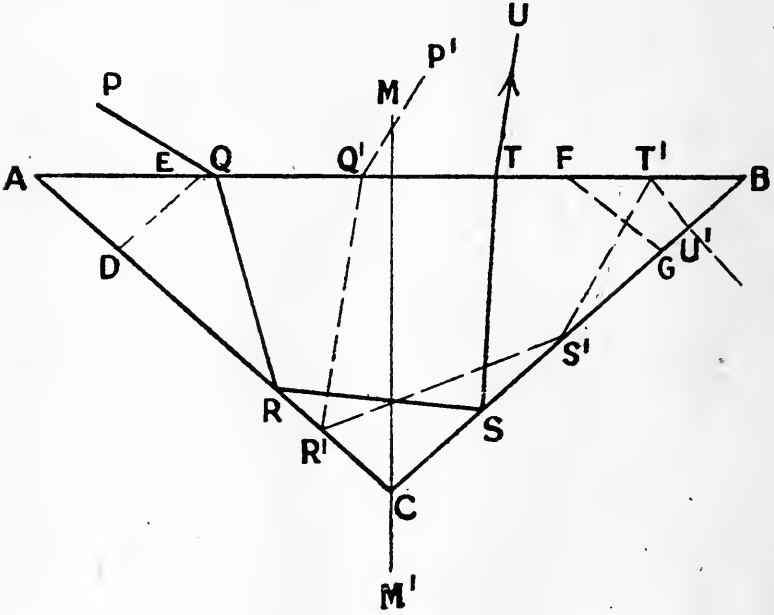


FIG. 29.

is so great that the small loss of light caused by that arrangement of the facets is insignificant: the leakage occurs through the facet CB, near C, where the introduction of the facet DE allows light to reach CB at an angle less than the critical. In a

brilliant, where CB is the section of the triangular side of an eight-sided pyramid, the area near the apex C is very small, and the leakage may therefore be considered negligible.

Second case: α is greater than 45°

In this case the path of a vertical ray will be as shown by $PQRST$ in fig. 30, and the optimum value for α , which may be calculated as before, will be

$$\alpha = 49^\circ 13' \quad . \quad . \quad . \quad (15)$$

As regards the vertical rays, this value gives a fire just as satisfactory as (14) ($\alpha = 40^\circ 45'$); let us consider what happens to oblique rays.

Rays incident from the left as $pqrst$ may strike BC at an angle of incidence less than the critical, and will then leak out backwards. Or they may be reflected along st , and may then be reflected into the stone. Both alternatives are undesirable, but they do not greatly affect the brilliancy of the gem, because, as we have seen, the amount of light incident from the left is small.

That incident from the right is, on the contrary, large.

Let us follow ray $P'Q'R'S'T'$. It will be reflected twice, and will leave the

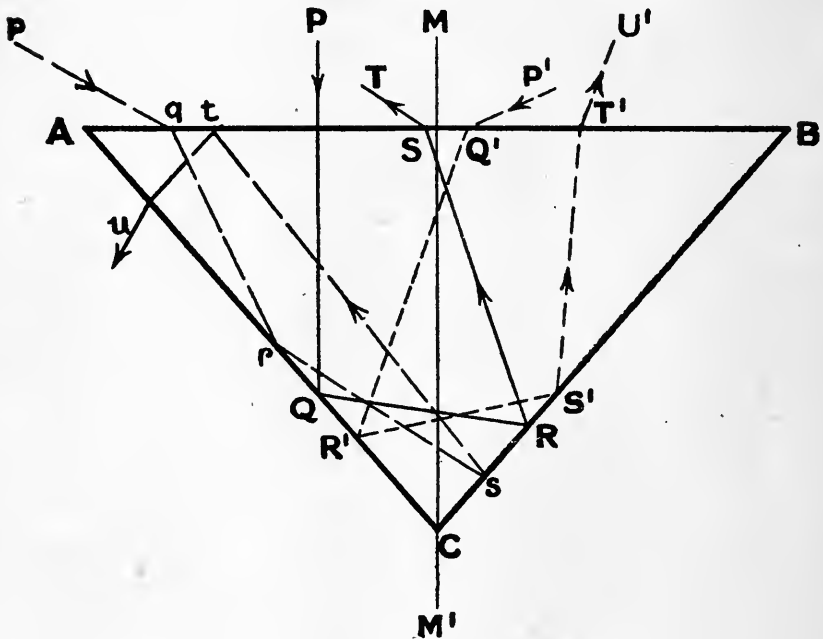


FIG. 30.

diamond after the second reflection, like the vertically incident ray, but with a smaller refraction, and consequently less fire; most of the light will be striking the face AB nearly vertically when leaving the stone, and the fire will be very small.

This time it is impossible to correct the defect by introducing accessory facets, as the paths $S'T'$ of the various oblique rays are not localised near the edge B , but are spread over the whole of the face; we are therefore forced to abandon this design.

Summary of the Results obtained for α

We have found that—

For first reflection, α must be greater than $48^\circ 52'$.

For second reflection, α must be less than $43^\circ 43'$.

For refraction, α may be less or more than 45° . When more, the best value is $49^\circ 15'$, but it is unsatisfactory. When less, the best value is $40^\circ 45'$, and is very satisfactory, as the light can be arranged to leave with the best possible dispersion.

Upon consideration of the above results, we conclude that the correct value for α is $40^\circ 45'$, and gives the most vivid fire and the greatest brilliancy, and that although a greater angle would give better reflection, this would not compensate for the loss due

to the corresponding reduction in dispersion. In all future work upon the modern brilliant we will therefore take

$$\alpha = 40^{\circ} 45'.$$

B. Front of the Brilliant

When arriving at the value of $\alpha = 40^{\circ} 45'$, we have explained how the use of that angle introduced defects which could be corrected by the use of extra facets. The section will therefore be shaped somewhat

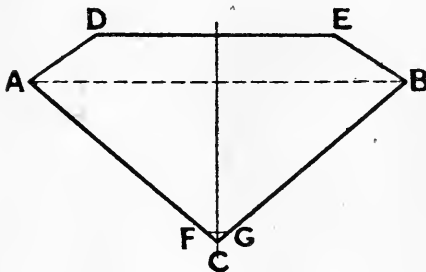


FIG. 31.

as in fig. 31. It will be convenient to give to the different facets the names by which they are known in the diamond-cutting industry. These are as follows:—

AC and BC are called pavilions or quoins, (according to their position relative to the axis of crystallisation of the diamond).

A D and E B are similarly called bezels or quoins.

D E is the table.

F G is the culet, which is made very small and whose only purpose is to avoid a sharp point.

Through A and B passes the girdle of the stone.

We have to find the proportions and inclination of the bezels and the table. These are best found graphically. We know that the introduction of the bezels is due to the oblique rays; it is therefore necessary to study the distribution of these rays about the table, and to find what proportion of them is incident in any particular direction.

Consider a surface A B (fig. 32) upon which a beam of light falls at an angle α . Let us rotate the beam so that the angle becomes β (for convenience, the figure shows the surface A B rotated instead to A' B, but the effect is the same). The light falling upon A B can be stopped in the first case by intercepting it with screen

BC, and in the second with a screen BC' where BCC' is at right angles to the direction of the beam.

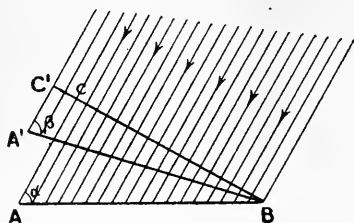


FIG. 32.

And if the intensity of the light is uniform, the length of BC and BC' will be a measure of the amount of light fall-

ing upon AB and AB' respectively.

Now

$$BC = AB \sin \alpha$$

$$BC' = A'B \sin \beta = AB \sin \beta.$$

Therefore, other things being equal, the amount of light falling upon a surface is proportional to the sine of the angle between the surface and the direction of the light.

We can put it as follows:—

If uniformly distributed light is falling from various directions upon a surface AB, the amount of light striking it from any particular direction will be proportional to the sine of the angle between the surface and that direction.

If we draw a curve between the amount of light striking a surface from any particular direction, and the angle between the surface and that direction, the curve will be a sine curve (fig. 33) if the light is equally distributed and of equal intensity in all directions.

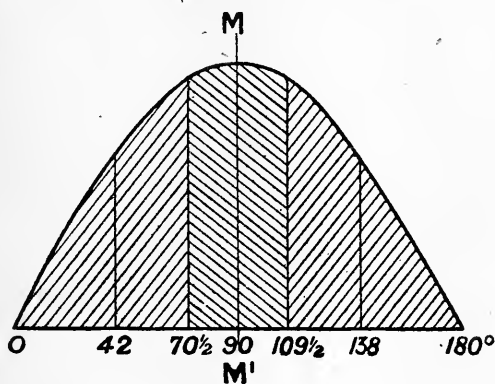


FIG. 33.

For calculations we can assume this to be the case, and we will take the distribution of the quantity of light at different angles to follow a sine law.

It is convenient to divide all the light entering a diamond into three groups, one of vertical rays and two of oblique rays, such that the amount of light entering from each group is the same. Now in the

sine curve (fig. 33) the horizontal distances are proportional to the angles between the table of a diamond and the direction of the entering rays; the vertical distances are proportional to the amount of light entering at these angles. The total amount of light entering will be proportional to the area shaded. That area must therefore be divided into three equal parts; this may be done by integrals, or by drawing the curve on squared paper, counting the squares, and drawing two vertical lines on the paper so that one-third of the number of the squares is on either side of each line.

By integrals,

$$\text{area} = \int \sin x \, dx = -\cos x.$$

$$\text{The total area} = [-\cos x]_0^{180} = 1 + 1 = 2,$$

therefore

$$\frac{1}{3} \text{ area} = \frac{2}{3}.$$

The value of α corresponding to the vertical dividing lines on the curve is thus given by

$$\cos x = 1 - \frac{2}{3} = \frac{1}{3}$$

$$\cos x = 1 - \frac{4}{3} = -\frac{1}{3},$$

therefore

$$x = 70\frac{1}{2}^\circ \text{ approximately}$$

and

$$x = 109\frac{1}{2}^\circ.$$

Taking the value $x = 90^\circ$ as zero for reckoning the angles of incidence,

$$i = 90^\circ - 70\frac{1}{2}^\circ = 19\frac{1}{2}$$

and

$$i = 90^\circ - 109\frac{1}{2}^\circ = -19\frac{1}{2}.$$

The corresponding angles of refraction are

$$\sin r = \frac{\sin i}{n} = \frac{\sin 19\frac{1}{2}^\circ}{2.417} = \frac{.3333}{2.417} = .1377$$

$$r = 7^\circ 52'.$$

The range of the different classes is thus as follows :—

Angle of incidence :

vertical rays $-19\frac{1}{2}^\circ$ to $+19\frac{1}{2}^\circ$

oblique rays -90° to $-19\frac{1}{2}^\circ$

and $+19\frac{1}{2}^\circ$ to $+90^\circ$.

Angle of refraction :

vertical rays $-7^\circ 52'$ to $+7^\circ 52'$

oblique rays $-24^\circ 26'$ to $-7^\circ 52'$

and $+7^\circ 52'$ to $+24^\circ 26'$.

The average angle of each of these classes

may be obtained by dividing each of the corresponding parts on the sine curve in two equal parts. The results are as follows :—

Angle of incidence :

vertical rays 0°
 oblique rays -42°
 and $+42^{\circ}$.

Angle of refraction :

vertical rays 0°
 oblique rays -16°
 and $+16^{\circ}$.

For the design of the table and bezels, we have to know the directions and positions of the rays leaving the stone. The values just obtained would enable us to do so if all the rays entering the front of the gem also left there. We have, however, adopted a value for α ($\alpha = 40^{\circ} 45'$) which we know permits leakage, and we have to take that leakage into consideration.

The angle where leakage begins is inclined at $24^{\circ} 26'$ to the pavilion (fig. 24). We have thus

$$Q' R' N' = 24^{\circ} 26',$$

therefore

$$Q' R' A' = 90^\circ - 24^\circ 26' = 65^\circ 34'.$$

Now in triangle A Q' R',

$$Q' R' A + A Q' R' + R' A Q' = 180^\circ,$$

therefore

$$\begin{aligned} A Q' R' &= 180^\circ - 65^\circ 34' - 40^\circ 45' \\ &= 73^\circ 41'. \end{aligned}$$

The limiting angle of refraction R' Q' T is thus

$$= 90^\circ - 73^\circ 41' = 16^\circ 19',$$

corresponding to an angle of incidence of

$$\begin{aligned} \sin i &= n \sin r = 2.417 \sin 16^\circ 19' \\ &= 2.417 \times .281 = .678. \\ i &= 42\frac{1}{2}^\circ. \end{aligned}$$

Upon referring to the sine curve, we find that the area shaded (fig. 34), which represents the amount of light lost by leakage, although not so large as if the same number of degrees leakage had occurred at the middle part of the curve, is still very appreciable, forming as it does about one-sixth of the total area. Just under one-half (exactly .493) of the light incident obliquely from the right (fig. 25) is effective,

the other half being lost by leakage. Still, the sacrifice is worth while, as it produces the best possible fire.

The oblique rays incident from the right range therefore $19\frac{1}{2}^{\circ}$ to $42\frac{1}{2}^{\circ}$, with an average (obtained as before) of $30^{\circ} 15'$. The corre-

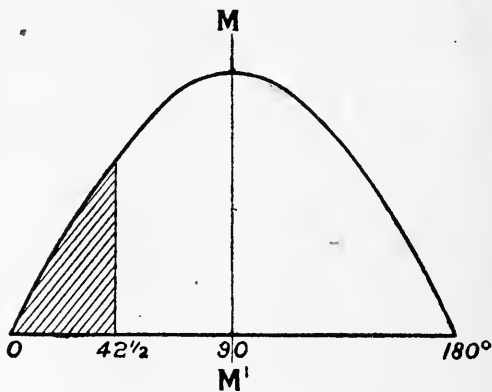


FIG. 34.

sponding refracted rays are $7^{\circ} 52'$, $16^{\circ} 19'$, and $12^{\circ} 0'$.


We have now all the information necessary for the design of the table and the bezels.

Design of Table and Bezels (fig. 35)

Let us start with the fundamental section ABC symmetrical about MM', making the angles ACB and ABC $40^{\circ} 45'$.

2 CAB

[To face p. 88.]

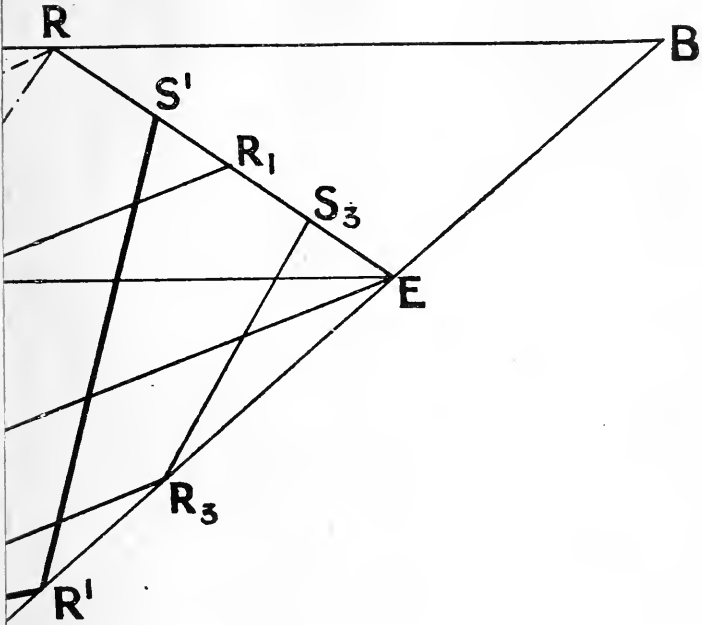

E. & F. N. SPON, LTD., LONDON.




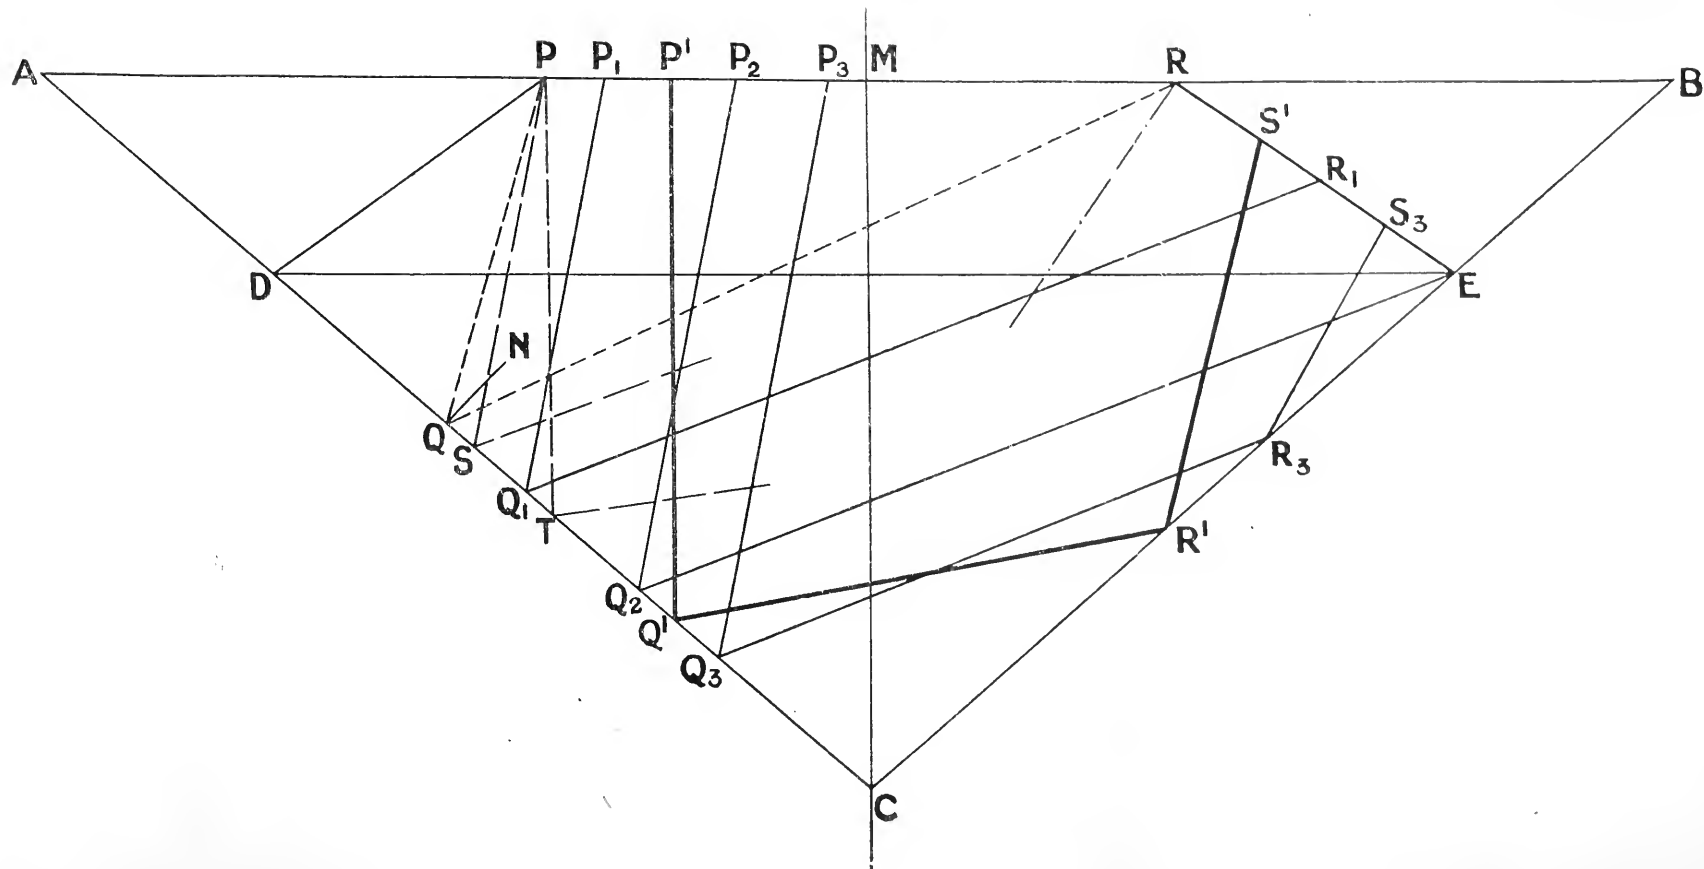


FIG. 35.

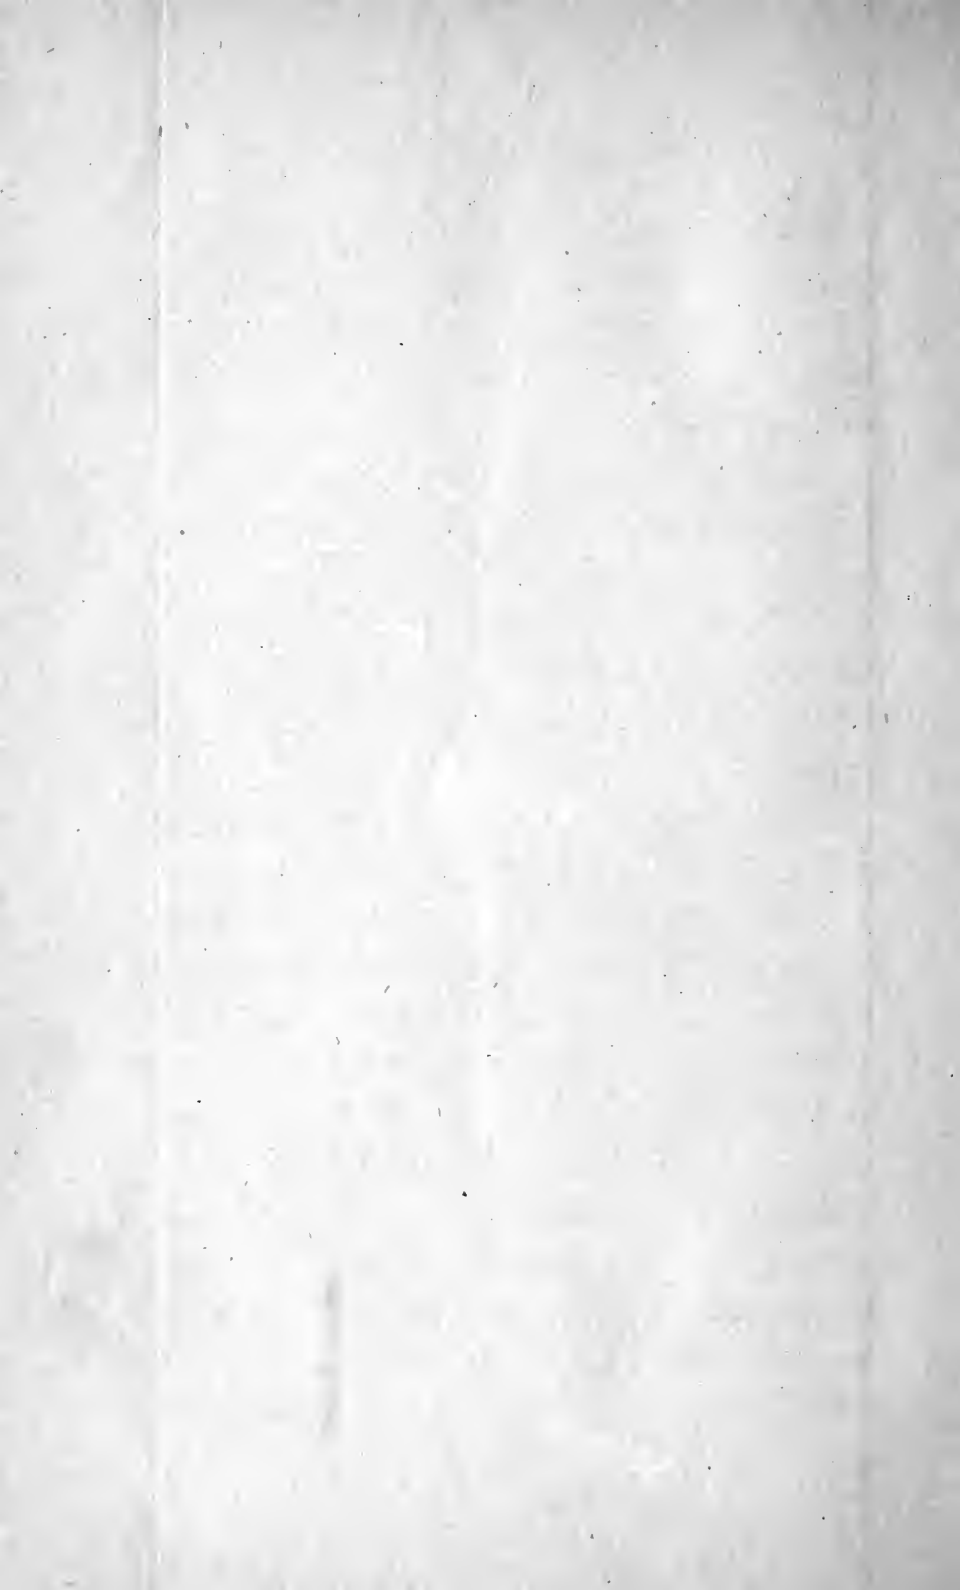

The bezels have been introduced into the design to disperse the rays which were originally incident from the right upon the facet AB . To find the limits of the table, we have therefore to consider the path of limiting oblique ray. We know that this ray has an angle of incidence of $42\frac{1}{2}^\circ$ and an angle of refraction of $16^\circ 19'$. Let us draw such a ray PQ : it will be totally reflected along QR , if we make $PQN = NQR$, where QN is the normal. Now QR should meet a bezel.

If the ray PQR was drawn such that $MP = MR$, then P and R will be the points at which the bezels should meet the table. For if PQ be drawn nearer to the centre of the stone, QR will then meet the bezel, and if PQ be drawn further away, it will meet the opposite bezel upon its entry into the stone and will be deflected.

The first point to strike us is that no oblique rays incident from the left upon the table strike the pavilion AB , owing to the fact that the table stops at P . We will, therefore, treat them as non-existent,

and confine our attention to the vertical rays and those incident from the right.

Let us draw the limiting average rays of these two groups, *i.e.* the rays of the average refractions 0° and 12° passing through P, P S, and P T. The length of the pavilion upon which the rays of these two groups fall are thus respectively CS and C T.

The rays of the first group P' Q' R' S' are all reflected twice before passing out of the stone, and make, after the second reflection, an angle of 17° with the vertical (as by eq. (12)). Of the rays of the second group, most are reflected once only (P₁ Q₁ R₁) and make then an angle of $69\frac{1}{2}^\circ$ with the vertical (this angle may be found by measurement or by calculation). Part of the second group is reflected twice (P₃ Q₃ R₃ S₃), and strikes the bezel at 29° to the vertical. This last part will be considered later, and may be neglected for the moment.

We have to determine the relation between the amount of light of the first group and of the first part of the second

group. Now we know that the amount of oblique light reflected from a surface on pavilion AC is .493 of the amount of vertical light reflected (cp. fig. 34 and context). If we take as limit for the once-reflected oblique ray the point E (as a trial) on pavilion BC, *i.e.* if it is at E that the girdle is situated, then the corresponding point of reflection for that oblique ray will be Q_2 (fig. 35). The surface of pavilion upon which the oblique rays then act will be limited by S and Q_2 , and as in a brilliant the face AC is triangular, the surface will be proportional to

$$\overline{SC^2} - \overline{Q_2C^2}.$$

Similarly, the surface upon which the vertical group falls will be proportional to

$$\overline{TC^2}.$$

Thus we have as relative amounts of light—

for vertical rays	$\overline{TC^2}$
for oblique rays	$\cdot 493(\overline{SC^2} - \overline{QC^2}).$

The first group strikes the bezel at 17°

to the vertical, and the second at $69\frac{1}{2}^\circ$ to the vertical. The average inclination to the vertical will thus be

$$\frac{17 \times \overline{TC}^2 + 69\frac{1}{2} \times .493(\overline{SC}^2 - \overline{QC}^2)}{\overline{TC}^2 + .493(\overline{SC}^2 - \overline{QC}^2)}$$

Let us draw a line in that direction (through R, say), and let us draw a perpendicular to it through R, RE; then that perpendicular will be the best direction for the bezel, as a facet in that direction takes the best possible advantage of both groups of rays.

If the point E originally selected was not correct, then the perpendicular through R will not pass through E, and the position of E has to be corrected and the corresponding value of CQ_2 correspondingly altered until the correct position of E is obtained.

For that position of E (shown on fig. 35), measures scaled off the drawing give

$$\begin{array}{l} CS = 2.67 \quad \overline{CS}^2 = 7.12 \\ CT = 2.13 \quad \overline{CT}^2 = 4.54 \quad \overline{CS}^2 - \overline{CQ}^2 = 4.57. \\ CQ_2 = 1.60 \quad \overline{CQ}_2^2 = 2.56 \end{array}$$

Therefore the average resultant inclination will be

$$\begin{aligned} & \frac{17 \times \overline{CT}^2 + 69\frac{1}{2} \times .493(\overline{CS}^2 - \overline{CQ}^2)}{(\overline{CT}^2 + .493(\overline{CS}^2 - \overline{CQ}^2))} \\ &= \frac{17 \times 4.54 + 69.5 \times .493 \times 4.57}{4.54 + .493 \times 4.57} \\ &= \frac{77.2 + 156.2}{4.54 + 2.24} = \frac{233.4}{6.78} = 34.45 = 34\frac{1}{2}^\circ \end{aligned}$$

to the vertical.

By the construction, the angle β , *i.e.* the angle between the bezel and the horizontal, has the same value

$$\beta = 34\frac{1}{2}^\circ.$$

The small proportion of oblique rays which are reflected twice meet the bezel near its edge, striking it nearly normally: they make an angle of 29° with the vertical. Facets more steeply inclined to the horizontal than the bezel should therefore be provided there. The best angle for refraction would be $29^\circ + 17^\circ = 46^\circ$, but if such an angle were adopted most of the light would leave in a backward direction, which is not desirable. It is therefore

advisable to adopt a somewhat smaller value ; an angle of about 42° is best.

FACETING

The faceting which is added to the brilliant is shown in fig. 43. Near the table, "star" facets are introduced, and near the girdle, "cross" or "half" facets are used both at the front and at the back of the stone.

We have seen that it is desirable to introduce near the girdle facets somewhat steeper than the bezel, at an angle of about 42° , by which facets the twice-reflected oblique rays might be suitably refracted. The front "half" facets fulfil this purpose.

We have remarked that the angle (42°) had to be made smaller than the best angle for refraction (46°) to avoid light being sent in a backward direction, where it is unlikely to meet either a spectator or a source of light.

To obviate this disadvantage, a facet two degrees steeper than the pavilion should be introduced near the girdle on the back

side of the stone; for then the second reflection of the oblique rays will send them at an angle of 25° to the vertical (instead of 29°), and the best value for refraction for the front half facets will be between

$$25^\circ + 17^\circ = 42^\circ.$$

These values are satisfactory also as regards the distribution of light; for now the greater part of the light is sent not in a backward, but in a forward, direction.

The facet two or three degrees steeper than the pavilion is obtained in the brilliant by the introduction of the back "half" facet, which is, as a matter of fact, generally found to be about 2° steeper than the pavilion in well-cut stones. Where the cut is somewhat less fine and the girdle is left somewhat thick (to save weight), that facet is sometimes made 3° steeper, or even more, than the pavilion.

The "star" facet was probably introduced to complete the design of the brilliant, which without its use would be lacking in harmony, but which its introduction makes

exceedingly pleasing from the point of view of the balance of lines.

Let us examine the optical consequences of the use of "star" facets.

On the one hand, their inclination—about 15° to the horizontal—permits a certain amount of light to leave the stone without being sufficiently refracted. On the other, they diminish the area of the bezels and consequently decrease the leakage of light which occurs through the bezel and the opposite pavilion (owing to the surfaces being nearly parallel). They also cause a somewhat better distribution of light, for they deflect part of the rays which would otherwise have increased the strength of the spectra refracted by the bezels, and create therewith spectra along other directions; it is true that, as seen above, these spectra will be shorter. But they will be more numerous; and though the "fire"—as consequent from the great dispersion of the rays of light—will be slightly diminished, the "life"—if we may term "life" the frequency with which a

single source of light will be reflected and refracted to a single spectator upon a rotation of the stone—will be increased to a greater degree. And if we take into account the decrease in the leakage of light, we may conclude that the introduction of the stars, on the whole, is decidedly advantageous in the brilliant.

BEST PROPORTIONS OF A BRILLIANT

We have thus as best section of a brilliant one as given in fig. 35, A B C D E, where

$$\alpha = 40^{\circ} 45'$$

$$\beta = 34^{\circ} 30'.$$

D E is obtained from P R in fig. 35.

If we make the diameter A B of the stone 100 units, then the main dimensions are in the following proportions (fig. 35):—

Diameter A B	.	.	.	100
Table D E	.	.	.	53.0
Total thickness M C	.	.	.	59.3
Thickness above girdle M M'				16.2
„ below „ M'C				43.1

Fig. 36 shows the outline of a brilliant with these proportions.

These proportions can be approximated as follows :—

In a well-cut brilliant the diameter of

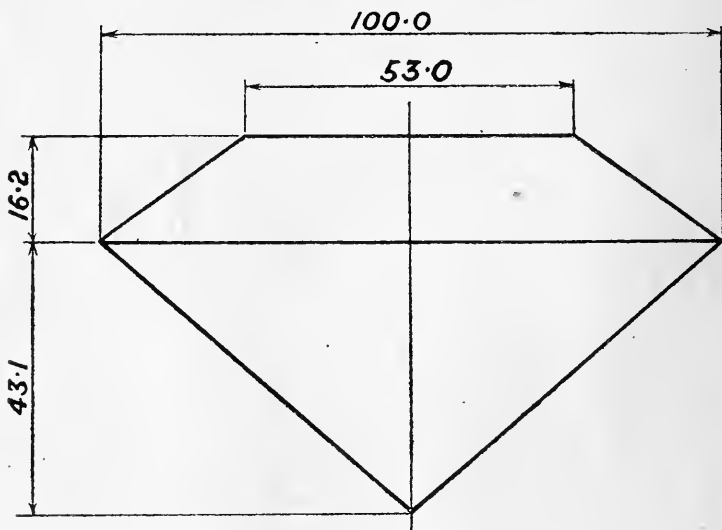


FIG. 36.

the table is one-half of the total diameter, and the thickness is six-tenths of the total diameter, rather more than one-quarter of the thickness being above the girdle and rather less than three-quarters below.

It is to be noted here that a different proportion is generally stated for the thickness

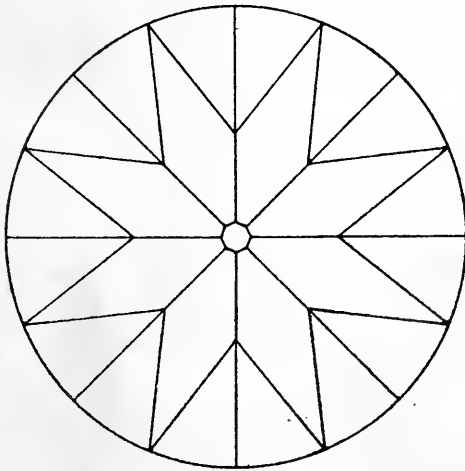
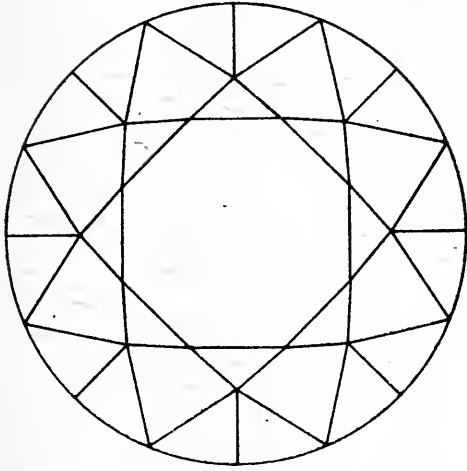


FIG. 37.

,,
,, ,
,, ,
,, ,
,, ,

above the girdle ("one-third of the total thickness"), both in works upon diamonds and by diamond polishers themselves. It is true that diamonds were cut thicker above the girdle and with a smaller table before the introduction of sawing, for then the table was obtained by grinding away a corner or an edge of the stone, and the loss in weight was thus considerable, and would have been very much greater still if the calculated proportions had been adopted. With the use of the saw, the loss in weight was enormously reduced and the manufacture of sawn stones became therefore much finer and more in accordance with the results given above. It is a remarkable illustration of conservatism that although diamonds have been cut for decades with $\frac{1}{4}$ (approximately) of the thickness above the girdle, yet even now the rule is generally stated as $\frac{1}{3}$ of the thickness.

Stones are still cut according to that rule, but then they are not sawn stones as a rule, and the thickness is left greater

to diminish the loss in weight. The brilliancy is not greatly diminished by making the stone slightly thicker over the girdle.

COMPARISON OF THE THEORETICALLY BEST VALUES WITH THOSE USED IN PRACTICE

In the course of his connection with the diamond-cutting industry the author has controlled and assisted in the control of the manufacture of some million pounds' worth of diamonds, which were all cut regardless of loss of weight, the only aim being to obtain the liveliest fire and the greatest brilliancy. The most brilliant larger stones were measured and their measures noted. It is interesting to note how remarkably close these measures, which are based upon empirical amelioration and rule-of-thumb correction, come to the calculated values.

As an instance the following measures, chosen at random, are given (the dimensions are in millimetres) :—

TABLE I

α . .	$40\frac{3}{4}^\circ$	$40\frac{3}{4}^\circ$	40°	41°	41°
β . .	35°	35°	$34\frac{1}{2}^\circ$	33°	34°
AB .	7.00	7.08	6.50	21.07	9.12
MC .	4.12	4.35	3.61	12.34	5.47
MM' .	1.08	1.32	0.85	3.31	1.61

These measures, worked out in percentage of AB, give :—

TABLE II

α .	$40\frac{3}{4}^\circ$	$40\frac{3}{4}^\circ$	40°	41°	41°	$40^\circ 42'$	$40^\circ 45'$
β .	35°	35°	$34\frac{1}{2}^\circ$	33°	34°	$34^\circ 18'$	$34^\circ 30'$
AB	100	100	100	100	100	100	100
MC	58.7	61.4	55.4	58.5	60	58.9	59.3
MM'	15.7	18.6	13.3	15.7	17.8	16.2	16.2
M'C	43.0	42.8	42.1	42.8	42.2	42.6	43.1

In the seventh column the averages of the measures are worked out, and the eighth gives the calculated theoretical values. It will be noted that the values of α , β , and MM' correspond very closely indeed, but

that MC and $M'C$ are very slightly less than they should be theoretically.

The very slight difference between the theoretical and the measured values is due to the introduction of a tiny facet, the collet, at the apex of the pavilions. This facet is introduced to avoid a sharp point which might cause a split or a breakage of the diamond.

What makes the agreement of these results even more remarkable is that in the manufacture of the diamond the polishers do not measure the angles, etc., by any instrument, but judge of their values entirely by the eye. And such is the skill they develop, that if the angles of two pavilions of a brilliant be measured, the difference between them will be inappreciable.

We may thus say that in the present-day well-cut brilliant, perfection is practically reached: the high-class brilliant is cut as near the theoretic values as is possible in practice, and gives a magnificent brilliancy to the diamond.

That some new shape will be evolved which will cause even greater fire and life than the brilliant is, of course, always possible, but it appears very doubtful, and it seems likely that the brilliant will be supreme for, at any rate, a long time yet.

(PR. 1605.)



LIBRARY OF CONGRESS



0 003 455 912 0